

CATALOG C-CRG-0906

CHEMICAL RESISTANCE GUIDE

FOR PLASTIC AND METAL
VALVES AND FITTINGS

NIBCO®
AHEAD OF THE FLOW®

Business-to-Business Solutions

Look to NIBCO for technology leadership.

The velocity with which e-business evolves demands that new products and services be continuously developed and introduced to keep our customers at the center of our business efforts. NIBCO provides an entire suite of business-to-business solutions that is changing the way we interact with customers.



NIBCOpartner.comSM is an exclusive set of secure web applications that allow quick access to customer-specific information and online order processing. This self-service approach gives you 24/7 access to your order status putting you in total control of your business.



Real time information includes:

- Online order entry
- Viewable invoices & reports
- Inventory availability
- Current price checks
- Order status
- Online library of price sheets, catalogs & submittals

Electronic Data Interchange (EDI) makes it possible to trade business documents at the speed of light. This technology cuts the cost of each transaction by eliminating the manual labor and paperwork involved in traditional order taking. This amounts to cost-savings, increased accuracy and better use of resources.

With EDI, you can trade:

- Purchase orders
- PO Acknowledgements
- Invoices
- Product activity data
- Advanced ship notices
- Remittance advice



Vendor Managed Inventory (VMI), a sophisticated service for automated inventory management, reduces your overhead by transferring inventory management, order entry and forecasting to NIBCO. This is an on-going, interactive partnership with NIBCO.

Through automation, VMI brings results:

- Improves customer service
- Optimum inventory efficiencies
- Better forecasting
- Cuts transaction costs
- Peace of mind
- Relief from day-to-day management



INTRODUCTION

This chemical resistance guide has been compiled to assist the piping system designer in selecting chemical resistant materials. The information given is intended as a guide only. Many conditions can affect the material choices. Careful consideration must be given to temperature, pressure and chemical concentrations before a final material can be selected.

Thermoplastics' and elastomers' physical characteristics are more sensitive to temperature than metals. For this reason, a rating chart has been developed for each.

MATERIAL RATINGS FOR THERMOPLASTICS & ELASTOMERS

| | |
|------------------|---|
| Temp. in °F | = "A" rating, maximum temperature which is recommended, resistant under normal conditions |
| B to Temp. in °F | = Conditional resistance, consult factory |
| C | = Not recommended |
| Blank | = No data available |

MATERIAL RATINGS FOR METALS

| | |
|-------|--|
| A | = Recommended, resistant under normal conditions |
| B | = Conditional, consult factory |
| C | = Not recommended |
| Blank | = No data available |

Temperature maximums for thermoplastics, elastomers and metals should always fall within published temp/pressure ratings for individual valves. **THERMOPLASTICS ARE NOT RECOMMENDED FOR COMPRESSED AIR OR GAS SERVICE.**

This guide considers the resistance of the total valve assembly as well as the resistance of individual trim and fitting materials. The rating assigned to the valve body plus trim combinations is always that of the least resistant part. In the cases where the valve body is the least resistant, there may be conditions under which the rate of corrosion is slow enough and the mass of the body large enough to be usable for a period of time. Such use should always be determined by test before installation of the component in a piping system.

In the selection of a butterfly valve for use with a particular chemical, the liner, disc, and stem must be resistant. All three materials should carry a rating of "A." The body of a properly functioning butterfly valve is isolated from the chemicals being handled and need not carry the same rating.

THERMOPLASTICS & ELASTOMERS

ABS — Acrylonitrile Butadiene Styrene Class 4-2-2 conforming to ASTM D1788 is a time-proven material. The smooth inner surface and superior resistance to deposit formation makes ABS drain, waste, and vent material ideal for residential and commercial sanitary systems. The residential DWV system can be exposed in service to a wide temperature span. ABS-DWV has proven satisfactory for use from -40°F to 180°F. These temperature variations can occur due to ambient temperature or the discharge of hot liquids

into the system. ABS-DWV is very resistant to a wide variety of materials ranging from sewage to commercial household chemical formulations. ABS-DWV is joined by solvent cementing or threading and can easily be connected to steel, copper, or cast iron through the use of transition fittings.

CPVC — Chlorinated Polyvinyl Chloride Class 23447-B, formerly designated Type IV, Grade 1 conforming to ASTM D-1784, has physical properties at 73°F similar to those of PVC, and its chemical resistance is similar to or generally better than that of PVC. CPVC, with a design stress of 2000 psi and maximum service temperature of 210°F, has proven to be an excellent material for hot corrosive liquids, hot or cold water distribution, and similar applications above the temperature range of PVC. CPVC is joined by solvent cementing, threading or flanging.

PP (Polypropylene) — Type 1 Polypropylene is a polyolefin, which is lightweight and generally high in chemical resistance. Although Type 1 polypropylene conforming to ASTM D-2146 is slightly lower in physical properties compared to PVC, it is chemically resistant to organic solvents as well as acids and alkalies. Generally, polypropylene should not be used in contact with strong oxidizing acids, chlorinated hydrocarbons, and aromatics. With a design stress of 1000 psi at 73°F, polypropylene has gained wide acceptance where its resistance to sulfur-bearing compounds is particularly useful in salt water disposal lines, crude oil piping, and low pressure gas gathering systems. Polypropylene has also proved to be an excellent material for laboratory and industrial drainage where mixtures of acids, bases, and solvents are involved. Polypropylene is joined by the thermo-seal fusion process, threading or flanging. At 180°F, or when threaded, PP should be used for drainage only at a pressure not exceeding 20 psi.

PVC — Polyvinyl Chloride Class 12454-B, formerly designated Type 1, Grade 1. PVC is the most frequently specified of all thermoplastic materials. It has been used successfully for over 30 years in such areas as chemical processing, industrial plating, chilled water distribution, deionized water lines, chemical drainage, and irrigation systems. PVC is characterized by high physical properties and resistance to corrosion and chemical attack by acids, alkalies, salt solutions, and many other chemicals. It is attacked, however, by polar solvents such as ketones, some chlorinated hydrocarbons and aromatics. The maximum service temperature of PVC is 140°F. With a design stress of 2000 psi, PVC has the highest long-term hydrostatic strength at 73°F of any of the major thermoplastics being used for piping systems. PVC is joined by solvent cementing, threading, or flanging.

PVDF (Polyvinylidene Fluoride) — KEM-TEMP (KYNAR®) is a strong, tough and abrasion-resistant fluorocarbon material. It resists distortion and retains most of its strength to 280°F. It is chemically resistant to most acids, bases, and organic solvents and is ideally suited for handling wet or dry chlorine, bromine and other halogens. No other solid thermoplastic piping components can approach the combination of strength, chemical resistance and working temperatures of PVDF. PVDF is joined by the thermo-seal fusion process, threading or flanging.

EPDM — EPDM is a terpolymer elastomer made from ethylene-propylene diene monomer. EPDM has good abrasion and tear resistance and offers excellent chemical resistance to a variety of acids and alkalines. It is susceptible to attack by oils and is not recommended for applications involving petroleum oils, strong

Material Definitions

acids, or strong alkalines. It has exceptionally good weather aging and ozone resistance. It is fairly good with ketones and alcohols and has an excellent temperature range from -20°F to 250°F.

HYPALON® (CSM) — Hypalon has very good resistance to oxidation, ozone, and good flame resistance. It is similar to neoprene except with improved acid resistance where it will resist such oxidizing acids as nitric, hydrofluoric, and sulfuric acid. Abrasion resistance of Hypalon is excellent, about the equivalent of nitriles. Oil and solvent resistance is somewhat between that of neoprene and nitrile. Salts have little if any effect on Hypalon. Hypalon is not recommended for exposure to concentrated oxidizing acids, esters, ketones, chlorinated, aromatic and nitro hydrocarbons. Hypalon has a normal temperature range of -20°F to 200°F.

NEOPRENE (CR) — Neoprenes were one of the first synthetic rubbers developed. Neoprene is an all-purpose polymer with many desirable characteristics and features high resiliency with low compression set, flame resistance, and is animal and vegetable oil resistant. Neoprene is principally recommended for food and beverage service. Generally, neoprene is not affected by moderate chemicals, fats, greases, and many oils and solvents. Neoprene is attacked by strong oxidizing acids, most chlorinated solvents, esters, ketones, aromatic hydrocarbons, and hydraulic fluids. Neoprene has a moderate temperature range of -20°F to 160°F.

NITRILE (NBR) — (BUNA-N) is a general purpose oil-resistant polymer known as nitrile rubber. Nitrile is a copolymer of butadiene and acrylonitrile and has a moderate temperature range of -20°F to 180°F. Nitrile has good solvent, oil, water, and hydraulic fluid resistance. It displays good compression set, abrasion resistance and tensile strength. Nitrile should not be used in highly polar solvents such as acetone and methyl ethyl ketone, nor should it be used in chlorinated hydrocarbons, ozone or nitro hydrocarbons.

FLUOROCARBON (FKM) (VITON®) (FLUOREL®) — Fluorocarbon elastomers are inherently compatible with a broad spectrum of chemicals. Because of this extensive chemical compatibility, which spans considerable concentration and temperature ranges, fluorocarbon elastomers have gained wide acceptance as a material of construction for butterfly valve o-rings and seats. Fluorocarbon elastomers can be used in most applications involving mineral acids, salt solutions, chlorinated hydrocarbons, and petroleum oils. They are particularly good in hydrocarbon service. Fluorocarbon elastomers have one of the broadest temperature ranges of any of the elastomers, -20°F to 300°F; however, they are not suited for steam service.

TEFLON® (PTFE) — Polytetrafluoroethylene has outstanding resistance to chemical attack by most chemicals and solvents. PTFE has a temperature rating of -20°F to 400°F in valve applications. PTFE, a self lubricating compound, is used as a seat material in ball valves.

PEEK (Polyetheretherketone) — PEEK is a high-performance engineered thermoplastic which can be used above the useful range of PTFE. PEEK has physical characteristics approaching some metals (approximately 30K tensile) and has excellent resistance to a wide range of organic and inorganic chemicals. PEEK can be used up to 550°F and is an excellent choice for heat transfer fluids, steam and hydrocarbon services.

GRAPHITE — Graphite is the packing and seal material of choice for most fire-rated products, primarily because of its high temperature rating of approximately 2000°F. Graphite has excellent chemical resistance, can retain compressibility at all temperatures

and has a low coefficient of friction. Graphite is not recommended for use in strong oxidizing atmospheres.

FLUOREL is a registered trademark of the 3M Company
HYPALON is a registered trademark of the DuPont Company
KYNAR is a registered trademark of ATOFINA Chemicals, Inc.
TEFLON is a registered trademark of the DuPont Company.
VITON is a registered trademark of the DuPont Company.

METALS USED IN VALVES & FITTINGS

ALUMINUM — A non-ferrous metal, very lightweight, approximately one-third as much as steel. Aluminum exhibits excellent atmospheric corrosion resistance, but can be very reactive with other metals. In valves, aluminum is mainly used as an exterior trim component such as a handwheel or an identification tag.

COPPER — Among the most important properties of wrot copper materials are their thermal and electrical conductivity, corrosion resistance, wear resistance, and ductility. Wrot copper performs well in high temperature applications and is easily joined by soldering or brazing. Wrot copper is exclusively used for fittings.

BRONZE — One of the first alloys developed in the bronze age is generally accepted as the industry standard for pressure-rated bronze valves and fittings. Bronze has a higher strength than pure copper, is easily cast, has improved machinability, and is very easily joined by soldering or brazing. Bronze is very resistant to pitting corrosion, with general resistance to most chemicals less than that of pure copper.

SILICONE BRONZE — Has the ductility of copper but much more strength. The corrosion resistance of silicon bronze is equal to or greater than that of copper. Commonly used as stem material in pressure-rated valves, silicon bronze has greater resistance to stress corrosion cracking than common brasses.

ALUMINUM BRONZE — The most widely accepted disc material used in butterfly valves, aluminum bronze is heat treatable and has the strength of steel. Formation of an aluminum oxide layer on exposed surfaces makes this metal very corrosion resistant. Not recommended for high pH wet systems.

BRASS — Generally good corrosion resistance. Susceptible to de-zincification in specific applications; excellent machinability. Primary uses for wrot brass are for ball valve stems and balls, and iron valve stems. A forging grade of brass is used in ball valve bodies and end pieces.

GRAY IRON — An alloy of iron, carbon and silicon; easily cast; good pressure tightness in the as-cast condition. Gray iron has excellent dampening properties and is easily machined. It is standard material for bodies and bonnets of Class 125 and 250 iron body valves. Gray iron has corrosion resistance that is better than steel in certain environments.

DUCTILE IRON — Has composition similar to gray iron. Special treatment modifies metallurgical structure, which yields higher mechanical properties; some grades are heat-treated to improve ductility. Ductile iron has the strength properties of steel using similar casting techniques to that of gray iron.

CARBON STEEL — Very good mechanical properties; good resistance to stress corrosion and sulfides. Carbon steel has high and low temperature strength, is very tough and has excellent fatigue strength. Mainly used in gate, globe, and check valves for applications up to 850°F, and in one-, two-, and three-piece ball valves.

Material Definitions and Standards

3% NICKEL IRON — Improved corrosion resistance over gray and ductile iron. Higher temperature corrosion resistance and mechanical properties. Very resistant to oxidizing atmospheres.

NICKEL-PLATED DUCTILE IRON — Nickel coatings have received wide acceptance for use in chemical processing. These coatings have very high tensile strength, 50 to 225 ksi. To some extent, the hardness of a material is indicative of its resistance to abrasion and wear characteristics. Nickel plating is widely specified as a disc coating for butterfly valves.

400 SERIES STAINLESS STEEL — An alloy of iron, carbon, and chromium. This stainless is normally magnetic due to its martensitic structure and iron content. 400 series stainless steel is resistant to high temperature oxidation and has improved physical and mechanical properties over carbon steel. Most 400 series stainless steels are heat-treatable. The most common applications in valves are for stem material in butterfly valves and backseat bushings and wedges in cast steel valves.

316 STAINLESS STEEL — An alloy of iron, carbon, nickel, and chromium. A nonmagnetic stainless steel with more ductility than 400SS. Austenitic in structure, 316 stainless steel has very good corrosion resistance to a wide range of environments, is not susceptible to stress corrosion cracking and is not affected by heat treatment. Most common uses in valves are stem, body and ball materials.

17-4 PH STAINLESS STEEL® — Is a martensitic precipitation/age hardening stainless steel, offering high strength and hardness. 17-4 PH withstands corrosive attack better than any of the 400 series stainless steels, and in most conditions its corrosion resistance closely approaches that of 300 series stainless steel. 17-4 PH is primarily used as a stem material for butterfly and ball valves.

ALLOY 20Cb-3® — This alloy has higher amounts of nickel and chromium than 300 series stainless steel and with the addition of columbium, this alloy retards stress corrosion cracking and has improved resistance to sulfuric acid. Alloy 20 finds wide use in all phases of chemical processing. Commonly used as interior trim on butterfly valves.

MONEL® — Is a nickel-copper alloy used primarily as interior trim on butterfly and ball valves. One of the most specified materials for corrosion resistance to sea and salt water. Monel is also very resistant to strong caustic solutions.

STELLITE® — Cobalt base alloy, one of the best all-purpose hard facing alloys. Very resistant to heat, abrasion, corrosion, impact, galling, oxidation, thermal shock and erosion. Stellite takes a high polish and is used in steel valve seat rings. Normally applied with transfer plasma-arc; Stellite hardness is not affected by heat treatment.

HASTELLOY C® — A high nickel-chromium molybdenum alloy, which has outstanding resistance to a wide variety of chemical process environments, including strong oxidizers such as wet chlorine, chlorine gas, and ferric chloride. Hastelloy C is also resistant to nitric, hydrochloric, and sulfuric acids at moderate temperatures.

17-4 PH STAINLESS STEEL is a registered trademark of Armco Steel Company
STELLITE is a registered trademark of the Cabott Company

ALLOY 20Cb-3 is a registered trademark of Carpenter Technology

HASTELLOY C is a registered trademark of Haynes International

MONEL is a registered trademark of International Nickel

MATERIAL DESIGNATIONS & ASTM STANDARDS FOR LISTED VALVE METALS

| | | | |
|-----------------|---|----------------------------|--|
| Aluminum | ASTM B-85 Die Cast | 3% Ni-Iron | ASTM A-126-Class B Modified |
| Copper | ASTM B-75 Wrot & ASTM B-88 | Ni-Plated Ductile Iron | ASTM B-320 Plating |
| Bronze | ASTM B-61 Cast ASTM B-62 Cast ASTM B-584, Alloy 844 | 400 Series Stainless Steel | ASTM B-582 Type 416 Wrot ASTM A-217-Grade CA-15 ASTM A-276 Type 410 Wrot |
| Silicon Bronze | ASTM B-98 Alloy B ASTM B-371 Wrot | 316 Stainless | ASTM 276 Type 316 ASTM A-351-Grade CF-8M |
| Aluminum Bronze | ASTM B-148 Cast ASTM B-150 Rod | 17-4 PH Stainless Steel | ASTM A-564 Type 630 |
| Brass | ASTM B-16 Wrot ASTM B-124 Forged | Alloy 20 | ASTM A-351-Grade CN-7M ASTM B-473 20Cb-3 |
| Gray Iron | ASTM A-126 Class B | Monel | ASTM B-164 ASTM 494 Grade M-35-1 |
| Ductile Iron | ASTM A-395 Heat Treated ASTM A-536 As Cast | Stellite | AWS 5.13 Hard Face |
| Carbon Steel | ASTM A-216-Grade WCB Cast ASTM A-105 Forged ASTM A-352-Grade LCB Cast | Hastelloy C | ASTM B-574 ASTM B-494 Grade CW-12 MW |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | | METALS | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|---------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------|----------------|----------|----------|----------|-------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE SS. | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Acetaldehyde CH ₃ CHO | Conc. | | | 120 | C | C | 350 | 200 | C | C | C | C | 275 | A | C | C | C | C | C | B | B | A | | | A | A | A | B | C | | |
| Acetamide CH ₃ CONH ₂ | | 73 | | 75 | 350 | 200 | C | C | C | C | C | B | 550 | | A | | A | | A | A | | | A | A | A | A | A | B | | | |
| Acetic Acid CH ₃ COOH | 25% | C | 180 | 73 | 200 | 350 | 180 | C | 150 | C | C | 550 | A | C | C | C | C | C | C | C | C | C | C | A | A | A | A | A | C | C | |
| Acetic Acid CH ₃ COOH | 50% | C | 140 | 73 | 200 | 350 | 140 | C | 73 | C | C | 550 | A | C | C | C | C | C | C | C | C | C | C | A | A | A | A | A | A | C | C |
| Acetic Acid CH ₃ COOH | 85% | C | 100 | 73 | 150 | 350 | 100 | C | 73 | C | C | 550 | A | C | C | C | C | C | C | C | C | C | C | A | A | A | A | A | A | C | C |
| Acetic Acid CH ₃ COO | Glacial | C | 100 | C | 100 | 350 | B to 100 | C | C | C | C | 550 | A | C | C | C | C | C | C | C | C | C | C | A | B | A | A | A | A | C | C |
| Acetic Anhydride (CH ₃ CO) ₂ O | | | C | C | 350 | C | 70 | 200 | B to 70 | C | 275 | A | C | C | C | C | C | C | C | C | C | C | C | B | B | B | B | B | A | B | C |
| Acetone CH ₃ COCH ₃ | | C | 73 | C | C | 350 | 130 | C | B to 70 | C | C | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A |
| Acetonitrile CH ₃ CN | | C | | C | 150 | | C | C | | 70 | C | 275 | | | | | | | | | | | | | A | A | A | A | A | A | |
| Acetophenone C ₆ H ₅ COCH ₃ | | | 120 | | C | 350 | 140 | C | | C | C | 275 | | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | |
| Acetyl Chloride CH ₃ COCl | | C | | | 125 | 200 | C | C | C | C | 185 | 275 | | A | A | A | A | C | C | A | C | C | A | A | A | A | A | A | C | A | |
| Acetylene HC = CH | Gas 100% | 70 | | 73 | 140 | 250 | 250 | 200 | 140 | 70 | 70 | 200 | 275 | | C | C | C | C | A | A | A | A | A | A | A | A | A | A | A | A | C |
| Acrylic Acid H ₂ C=CHCOOH | 97% | | | C | 150 | 200 | | | | | | | A | | | | | | | | | | | | | | | | | | |
| Acrylonitrile H ₂ C=CHCN | | C | | C | 73 | 350 | C | C | 140 | C | C | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | B | | |
| Adipic Acid COOH(CH ₂) ₄ COOH | Sat'd. | 185 | | 140 | 150 | 350 | 200 | 180 | 140 | 160 | 250 | 275 | | | | | | C | C | B | C | B | C | B to 200 | B | B to 200 | A | B | A | | |
| Allyl Alcohol CH ₂ =CHCH ₂ OH | 96% | C | C | 140 | C | 125 | 250 | 70 | 160 | 70 | B to 70 | 100 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Allyl Chloride CH ₂ CHCH ₂ Cl | | | | C | 212 | 350 | C | C | | 70 | 275 | | | | | | | | C | | | | | | | | | | C | | |
| Aluminum Acetate Al(C ₂ H ₅ O ₂) ₃ | Sat'd. | | | | | 275 | 350 | 200 | B to 70 | C | C | C | | | C | C | C | C | C | C | C | C | C | A | A | B | C | C | | | |
| Aluminum Ammonium Sulfate (Alum) AlNH ₄ (SO ₄) ₂ 12H ₂ O | Sat'd. | | 180 | 150 | 140 | 275 | 250 | 200 | 140 | | | 200 | | A | B | B | B | B | C | | | B | A | A | A | A | A | A | B | | |
| Aluminum Chloride Aqueous AlCl ₃ | Sat'd. | | 185 | 180 | 140 | 280 | 250 | 210 | 70 | 200 | 160 | 250 | 275 | A | C | C | C | C | C | C | C | C | C | A | C | A | A | A | A | C | |
| Aluminum Fluoride Anhydrous AlF ₃ | Sat'd. | | | 73 | 280 | 250 | 210 | 180 | 200 | 160 | 250 | | A | C | C | C | C | C | C | C | C | C | B | C | B | B | A | C | | | |
| Aluminum Hydroxide AlO ₃ • ₃ H ₂ O | Sat'd. | | 185 | 140 | 140 | 280 | 250 | 210 | 180 | | 100 | 200 | | C | C | C | C | B | B | C | B | B | A | A | A | B | | C | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|---------|---------|----------|--------------|------|------------------------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------------------|----------|---------|----------|-------|----------|-------------|----------|---------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (65% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | COPPER STEEL | 3% NI/IRON | NI PLATED DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Aluminum Nitrate <chem>Al(NO3)3·H2O</chem> | Sat'd. | 185 | 180 | 140 | 280 | 250 | 210 | 180 | 100 | 100 | 100 | 100 | | A | C | C | C | C | C | C | C | A | A | A | C | | C | C | | | |
| Aluminum Oxychloride | | | | 140 | 275 | | | | | C | | | | | | | | | | | | | | | | | | | | | |
| Aluminum Potassium Sulfate (Alum) <chem>AlK(SO4)·12H2O</chem> | Sat'd. | 180 | 150 | 140 | 280 | 400 | 200 | 180 | 200 | 160 | 200 | | | A | B | B | B | B | | C | | B | A | A | A | A | A | B | | | |
| Aluminum Sulfate (Alum) <chem>Al2(SO4)3</chem> | Sat'd. | 185 | 180 | 140 | 280 | 250 | 210 | 200 | 160 | 140 | 185 | 275 | | A | C | C | C | C | C | C | C | C | C | B | B | | A | C | | | |
| Ammonia, Aqueous | | | | | | | | | | | | | | See Ammonium Hydroxide | | | | | | | | | | | | | | | | | |
| Ammonia Gas <chem>NH3</chem> | 100% | | C | 150 | 140 | C | 400 | 140 | 140 | 140 | 140 | C | 550 | A | B | | | C | A | | A | | | A | A | A | A | A | B | B | |
| Ammonia Liquid <chem>NH3</chem> | 100% | C | C | 73 | C | C | 400 | 140 | B to 70 | 70 | 70 | C | 275 | A | C | C | C | C | | A | | | A | A | A | A | A | A | A | C | |
| Ammonium Acetate <chem>NH4(C2H3O2)</chem> | Sat'd. | | | 73 | 140 | 175 | 400 | 140 | | 140 | 140 | | | | C | C | C | C | | | | | B | | B | | | | | | |
| Ammonium Bifluoride <chem>NH4HF2</chem> | Sat'd. | 185 | | 140 | 150 | 400 | 200 | 180 | | | 200 | | A | C | | | C | C | C | C | C | C | B | B | B | B | | | B to 70 | | |
| Ammonium Bisulfide <chem>(NH4)HS</chem> | | | | | 140 | 280 | 400 | | 180 | | | | | | | | | | | | | | | | | | | | | | |
| Ammonium Carbonate <chem>CH3O2·2H3N</chem> | Sat'd. | | | 180 | 140 | 280 | 400 | 210 | | 140 | 140 | 250 | 275 | | C | | | C | | | A to 140 | C | | B | B | B | B | B | A | B to 212 | B to 70 |
| Ammonium Chloride <chem>NH4Cl</chem> | Sat'd. | 185 | 180 | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 250 | 275 | A | C | | | C | C | C | C | C | C | B | C | B | B | B | B | B | B | |
| Ammonium Dichromate <chem>(NH4)2Cr2O7</chem> | | | | | 73 | 250 | | 70 | 100 | 100 | 100 | | | A | | | | | | | | | | | | | | | | | |
| Ammonium Fluoride <chem>NH4F</chem> | 10% | | | | 140 | 280 | 400 | 210 | 100 | 200 | 100 | | | A | C | | | C | | | C | | | C | | | | | C | C | |
| Ammonium Fluoride <chem>NH4F</chem> | 25% | | | | 73 | 280 | 400 | 140 | | | | | | A | C | | | C | | | C | | | C | | | | | C | C | |
| Ammonium Hydroxide <chem>NH4OH</chem> | 10% | C | C | 180 | 140 | 225 | 400 | 210 | B to 70 | 200 | 150 | 70 | 550 | A | C | C | | C | | | C | | B | A | A | A | B | A | B | C | |
| Ammonia Hydroxide <chem>NH4OH</chem> | Sat'd. | C | C | 180 | 100 | 225 | 400 | 175 | C | 200 | 150 | C | 550 | A | C | C | | | | C | | B to 70 | A to 140 | | B | | B | B to 120 | C | | |
| Ammonium Nitrate <chem>NH4NO3</chem> | Sat'd. | 175 | 185 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | 100 | | A | C | C | | C | | | | | | A | A | A | A | A | C | | |
| Ammonium Persulphate <chem>(NH4)2S2O8</chem> | | | | | 73 | 150 | 140 | 73 | 200 | 210 | | 70 | 70 | | | C | C | C | C | C | C | C | C | B | A | A | A | C | A | C | C |
| Ammonium Phosphate (Monobasic) <chem>NH4H2PO4</chem> | All | | | | 140 | 280 | 400 | 210 | 100 | 140 | 140 | 185 | | A | C | C | C | C | B | B | C | | B | A | A | A | B | A | B | C | |
| Ammonium Sulfate <chem>(NH4)2SO4</chem> | | | | | 185 | 180 | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 200 | | A | C | C | C | B | B | C | B | B | B | B | A | B | A | C | C |
| Ammonium Sulfide <chem>(NH4)2S</chem> | Dilute | | | | | 125 | 350 | 210 | 140 | 200 | 160 | | | | C | C | C | C | C | C | C | C | C | B | B | B | B | B | A | A | C |
| Ammonium Thiocyanate <chem>NH4SCN</chem> | 50-60% | | | | | 140 | 275 | | 70 | 70 | 70 | 185 | | C | C | C | C | C | C | C | C | C | A | A | A | B | A | A | B | C | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | METALS | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|--------------------------------|--------|---------|----------|---------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|------------------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Amyl Acetate <chem>CH3COOC5H11</chem> | | | | C | C | 125 | 100 | B to 70 | C | C | C | C | 550 | | B | B | B | B | B | B | B | A | B | A | A | A | A | A | A | A |
| Amyl Alcohol <chem>C5H11OH</chem> | | | 73 | 180 | 100 | 280 | 400 | 210 | B to 140 | 200 | 140 | 185 | 550 | A | A | A | A | A | B | B | B | B | A | A | A | A | A | A | A | |
| n-Amyl Chloride <chem>C5H11Cl</chem> | | C | C | C | 280 | 400 | C | C | C | C | 200 | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | C | | |
| Aniline <chem>C6H5NH2</chem> | | C | 180 | C | 120 | 200 | 140 | C | 70 | C | C | 275 | A | C | C | C | C | B | B | C | B | B | A | A | A | B | A | C | C | |
| Aniline Chlorohydrate | | | | C | | | | | | | | | | | | | | | | | | | | | | | | A | | |
| Aniline Hydrochloride <chem>C6H5NH2•HCl</chem> | Sat'd. | C | | C | 75 | | | | C | C | 185 | | C | C | C | C | C | C | C | C | C | C | C | C | C | C | A | | | |
| Anthraquinone <chem>C14H8O2</chem> | | | | | 140 | | | | | | 200 | | | | C | C | C | | | | | | | | | | | | | |
| Anthraquinone Sulfonic Acid <chem>C14H7O2•SO3H•3H2O</chem> | | | | | 140 | | | | | | 200 | | | | | | | | | | | | | | | | | | | |
| Antimony Trichloride <chem>SbCl3</chem> | Sat'd. | | 180 | 140 | 73 | | 140 | 140 | 140 | 140 | 185 | 275 | A | C | C | C | C | C | C | C | C | C | C | C | C | A | A | C | | |
| Aqua Regia (Nitrohydrochloric Acid) <chem>CIHHNO3</chem> | C | 73 | C | C | 73 | 200 | C | C | B to 70 | C | 100 | C | C | C | C | C | C | C | C | C | C | C | C | C | B | B | B | C | | |
| Argon Ar | Dry | | | | | 350 | 200 | | | 100 | 200 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Arsenic Acid <chem>H3ASO4•1/2H2O</chem> | 80% | 185 | | 140 | 280 | 400 | 185 | 160 | 200 | 180 | 200 | | A | C | C | C | C | C | C | C | C | B | A | B | A | A | A | C | | |
| Aryl Sulfonic Acid <chem>C6H5SO3H</chem> | | | | | 140 | | | 140 | | | | 185 | | | | | | | | | | | | | | | | | | |
| Asphalt | | C | | C | 250 | 350 | C | B to 70 | C | C | 180 | | | A | A | A | A | A | A | A | A | A | A | A | A | B | A | C | A | |
| Barium Carbonate <chem>BaCO3</chem> | Sat'd. | | | | 140 | 280 | 400 | 250 | 180 | 200 | 160 | 250 | | A | A | A | A | A | B | B | B | B | A | A | A | A | A | A | | |
| Barium Chloride <chem>BaCl2•H2O</chem> | Sat'd. | 180 | 180 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | 300 | 275 | A | A | A | A | A | B | B | C | B | B | B | A | A | A | A | | |
| Barium Hydroxide <chem>Ba(OH)2</chem> | Sat'd. | 180 | 180 | 180 | 140 | 280 | 400 | 180 | 140 | 150 | 150 | 250 | | C | C | C | C | B | B | C | B | B | A | A | A | A | A | A | | |
| Barium Nitrate <chem>Ba(NO3)2</chem> | Sat'd. | 180 | 70 | 73 | 275 | 250 | 200 | 180 | 200 | 160 | 300 | 300 | | A | C | C | C | C | A | A | A | A | A | A | A | A | A | A | | |
| Barium Sulfate <chem>BaSO4</chem> | Sat'd. | 150 | 185 | C | 140 | 280 | 400 | 200 | 100 | 200 | 160 | 300 | 550 | A | B | B | B | B | B | B | A | B | A | A | A | A | A | A | | |
| Barium Sulfide <chem>BaS</chem> | Sat'd. | 150 | 180 | 180 | 140 | 280 | 400 | 140 | C | 200 | 160 | 300 | 275 | C | C | C | C | B | B | C | B | C | B | A | A | A | A | C | | |
| Beer | | C | | 180 | 140 | 200 | 300 | 200 | 70 | 200 | 140 | 200 | | A | A | A | A | C | C | C | C | A | A | A | A | A | A | A | | |
| Beet Sugar Liquors | | | | | 180 | 140 | 225 | | 210 | 100 | 200 | 160 | 185 | | | | | A | B | B | B | | | A | A | A | A | A | | |
| Benzaldehyde <chem>C6H5CHO</chem> | 10% | C | | 73 | 73 | 70 | | 140 | C | C | C | C | 275 | A | A | A | A | A | C | C | B | C | A | A | A | B | A | A | | |
| Benzene <chem>C6H6</chem> | | C | C | C | C | 170 | 250 | C | C | C | C | 150 | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|----------|----------|----------|----------|--------------|------|----------|---|----------------|-----------------|-------|-----------|--------------|--------------|------------|---------------------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|---|---|--|--|--|--|--|--|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROXYL | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NIPLATED DUCTILE IRON SERIES 400 S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER | | | | | | | | |
| Benzene Sulfonic Acid <chem>C6HSO3H</chem> | 10% | | | 180 | 140 | 125 | | C | C | 180 | 100 | 185 | 550 | | B | B | B | B | C | C | C | C | C | B | B | A | A | | | | | | | | | | | | |
| Benzoic Acid <chem>C6H5COOH</chem> | All | 73 | 73 | 140 | 140 | 230 | 350 | C | C | 160 | 200 | 250 | 550 | | C | C | C | C | C | C | C | C | C | A | A | A | A | A | A | A | | | | | | | | | |
| Benzyl Alcohol <chem>C6H5CH2OH</chem> | | C | C | 120 | C | 250 | 400 | C | C | C | C | 140 | 275 | | A | A | A | A | B | B | B | B | B | A | A | A | A | A | A | A | | | | | | | | | |
| Bismuth Carbonate <chem>(BiO)2CO3</chem> | | | | 140 | | | | 70 | 100 | 70 | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Black Liquor | Sat'd. | 185 | | 140 | 175 | 225 | 180 | 180 | 70 | 70 | 200 | | | C | C | C | C | B | B | B | B | B | B | A | B | A | B | | | | | | | | | | | | |
| Bleach | | | | | | | | | | | | | | | See Sodium Hypochlorite or Calcium Hypochlorite | | | | | | | | | | | | | | | | | | | | | | | | |
| Blood | | | | | | | 200 | | 70 | 70 | 70 | 70 | | | B | | B | | C | C | | | B | | A | A | A | A | A | A | A | | | | | | | | |
| Borax <chem>NaB4O7•10H2O</chem> | Sat'd. | | | 180 | 140 | 280 | | 210 | 140 | 200 | 140 | 185 | | | A | A | A | A | A | A | B | A | A | A | A | A | A | A | A | A | A | A | A | | | | | | |
| Boric Acid <chem>H3BO3</chem> | Sat'd. | 185 | 180 | 140 | 280 | | 210 | 140 | 200 | 140 | 185 | 275 | A | B | B | B | B | C | C | B | C | B | A | B | A | A | A | A | A | A | A | A | | | | | | | |
| Brake Fluid | | | | | | | 300 | 140 | C | | C | 275 | | B | | | | B | B | A | | B | A | A | A | A | A | A | A | A | A | A | | | | | | | |
| Brine | Sat'd. | 185 | 180 | 140 | 280 | 400 | 250 | 180 | 180 | 160 | 300 | | | A | A | A | | C | C | C | B | C | B | A | B | A | A | A | A | A | A | | | | | | | | |
| Bromic Acid <chem>HBrO3</chem> | | 185 | | 140 | 200 | | 70 | | | 70 | | | C | C | C | C | | | | | | | | | | | | | | | | C | C | | | | | | |
| Bromine <chem>Br2</chem> | Liquid | C | C | C | C | 150 | 300 | C | C | 70 | C | 70 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | A | C | C | | | | | | |
| Bromine <chem>Br2</chem> | Gas | C | C | C | C | 150 | 200 | C | C | 70 | C | 70 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | A | C | C | | | | | | |
| Bromine Water | Cold Sat'd. | C | 70 | C | 70 | 212 | 300 | C | C | 70 | C | 185 | C | C | C | C | C | C | C | C | C | C | C | C | C | | | | | | C | C | | | | | | | |
| Bromobenzene <chem>C6H7Br</chem> | | C | C | C | C | 150 | 120 | C | C | C | C | 150 | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Bromotoluene <chem>C7H7Br</chem> | | C | C | C | C | 175 | 70 | C | C | C | C | C | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Butadiene <chem>H2C=CHCH=CH2</chem> | 50% | 73 | C | 140 | 250 | C | C | B to 140 | | 140 | 185 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | | | | | |
| Butane <chem>C4H10</chem> | 50% | | 73 | 140 | 250 | 350 | C | 70 | 200 | 70 | 185 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | | | | | | |
| Butyl Acetate <chem>CH3COOCH(CH3)C2H5</chem> | | | 73 | C | C | 73 | 175 | 140 | C | C | C | 550 | | B | B | B | B | B | B | B | B | B | B | B | B | B | B | B | B | A | | | | | | | | | |
| Butyl Alcohol <chem>CH3(CH2)2CH2OH</chem> | | C | 100 | 100 | 100 | 225 | 300 | 200 | B to 140 | 140 | 140 | 75 | 550 | A | B | B | B | | B | | | A | A | A | A | A | A | A | A | A | B | | | | | | | | |
| Butyl Cellosolve <chem>HOCH2CH2OC4H9</chem> | | | | | 73 | | 200 | 140 | C | 100 | | C | | A | A | A | A | A | A | A | | | A | A | A | A | A | A | A | A | A | | | | | | | | |
| n-Butyl Chloride <chem>C4H9Cl</chem> | | | | | | 280 | 400 | C | C | C | 100 | | | B | B | B | B | B | B | B | | | B | B | B | B | B | B | B | B | B | | | | | | | | |
| Butylene (C) <chem>CH3CH:CHCH3</chem> | Liquid | | | | 140 | 280 | 400 | C | 70 | C to 100 | C | 100 | | | A | A | A | A | | | | | A | | A | A | A | A | A | A | A | A | | | | | | | |
| Butyl Phenol <chem>C6H5C6H4OH</chem> | | | | | 73 | 230 | | | B to 70 | C | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Butyl Phthalate | | | | | 180 | | | | | | | 70 | 275 | | | A | A | A | A | B | B | | | B | A | A | A | A | A | A | | | | | | | | | |
| Butyl Stearate <chem>CH3(CH2)16CO2(CH2)3CH3</chem> | | | | | 73 | 100 | 250 | C | 100 | | C | 185 | | | A | A | A | A | B | B | | | B | A | A | A | A | A | A | | | | | | | | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|--|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER | |
| Butynediol HOCH ₂ C:CH ₂ OH | | | | | 73 | | | | | 100 | B to 70 | | | | | | | | | | | | | | | | | | | | | | |
| Butyric Acid CH ₃ CH ₂ CH ₂ COOH | | | 180 | 73 | 230 | 300 | 140 | | C | C | 70 | 550 | | | A | A | A | A | A | C | C | C | C | B | A | A | A | A | | | | | |
| Cadmium Cyanide Cd(CN) ₂ | | 185 | | 140 | | | | | | 70 | | | | | | | | | | | | | | | | | | | | | | | |
| Calcium Bisulfide Ca(HS) ₂ •H ₂ O | | | | C | 280 | 200 | | | 100 | C | | 185 | | | | | | | | | | | | | | A | A | | | | | | |
| Calcium Bisulfite Ca(HSO ₃) ₂ | | 185 | 180 | 140 | 280 | 350 | C | 70 | 200 | 70 | 185 | | | | C | C | C | C | C | C | C | C | C | C | B | A | | A | C | A | | | |
| Calcium Carbonate CaCO ₃ | | 185 | 180 | 140 | 280 | 350 | 210 | 100 | 70 | 70 | 300 | 275 | | | C | C | C | C | C | B | B | B | B | B | A | A | A | A | A | A | | | |
| Calcium Chlorate Ca(ClO ₃) ₂ •H ₂ O | | | | | 140 | 280 | 350 | 140 | 70 | 70 | 70 | 185 | | | 140 | B | B | B | B | B | B | B | B | B | A | | A | A | | C | | | |
| Calcium Chloride CaCl ₂ | | 100 | 185 | 180 | 140 | 280 | 350 | 210 | 100 | 200 | 160 | 250 | 550 | A | B | B | B | B | A | A | C | | | C | B | A | B | A | A | B | | | |
| Calcium Hydroxide Ca(OH) ₂ | | | 185 | 180 | 140 | 280 | 250 | 210 | 140 | 200 | 70 | 250 | 275 | | C | C | C | C | C | C | C | C | C | C | A | A | A | A | A | A | C | | |
| Calcium Hypochlorite Ca(OCl) ₂ | 30% | 185 | 150 | 140 | 200 | 200 | 70 | C | 140 | | 185 | 275 | 90 | C | C | C | C | C | C | C | C | C | C | B | B | B | B | C | B | C | | | |
| Calcium Nitrate Ca(NO ₃) ₂ | | | | | 180 | 140 | 280 | 200 | 210 | 180 | 100 | 100 | 200 | | C | B | B | B | B | B | B | B | B | A | | A | A | | | B | | | |
| Calcium Oxide CaO | | | | | | 140 | 250 | | 210 | 180 | 200 | 160 | | | | | | | | | | | | | | A | A | B | | A | A | A | |
| Calcium Sulfate CaSO ₄ | | 100 | | | | 140 | 280 | 200 | 210 | 180 | 200 | 160 | 200 | | A | A | B | B | B | A | A | B | A | A | A | A | A | A | A | A | A | | |
| Camphor C ₁₀ H ₁₆ O | | C | | | 73 | | 350 | 210 | 100 | 70 | C | 250 | 550 | | B | B | B | B | B | B | B | B | B | A | A | A | A | A | B | | | | |
| Cane Sugar C ₁₂ H ₂₂ O ₁₁ | | | | | 73 | 140 | 275 | 400 | 250 | 180 | 100 | 160 | 200 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Caprylic Acid CH ₃ (CH ₂) ₆ COOH | | | | | | | 175 | 350 | | | | | | | | | | | | | | | | | A | A | B | | A | A | | | |
| Carbitol | | | | | 73 | | 200 | 70 | 70 | 70 | 70 | 100 | | | B | B | B | B | B | B | B | B | B | B | B | B | B | B | B | B | | | |
| Carbon Dioxide CO ₂ | Dry 100% | 100 | 185 | 150 | 140 | 20 | 400 | 200 | 180 | 200 | 160 | 200 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Carbon Dioxide CO ₂ | Wet | 100 | 185 | 150 | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 200 | 550 | A | A | A | A | A | A | B | B | B | B | B | A | A | A | A | A | A | | | |
| Carbon Disulfide CS ₂ | | | | | C | C | 73 | 200 | C | B to 70 | C | C | 70 | 275 | A | B | B | B | B | A | A | A | A | A | A | A | A | A | A | C | | | |
| Carbon Monoxide CO | Gas | 185 | | 140 | 275 | 400 | 250 | 70 | 200 | 70 | 250 | 550 | A | A | A | A | A | A | A | A | B | | | A | A | A | A | A | A | A | | | |
| Carbon Tetrachloride Cl ₄ | | C | 73 | C | 73 | 280 | 350 | C | C | C | C | 185 | 550 | A | A | A | A | A | C | C | A | | C | A | A | A | A | A | A | B | | | |
| Carbonic Acid H ₂ CO ₃ | Sat'd. | 185 | | 140 | 280 | 350 | 210 | 180 | 70 | 70 | 200 | 275 | A | C | C | C | C | B | B | B | B | B | A | A | A | A | A | B | | | | | |
| Castor Oil | | C | | 140 | 280 | 350 | 140 | 140 | 150 | 100 | | | A | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Caustic Potash | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Caustic Soda | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Cellosolve C ₄ H ₁₀ O ₂ | | | | | | 73 | 280 | 200 | 140 | C | 70 | | C | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | | | |

See Potassium Hydroxide

See Sodium Hydroxide

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------------|------------|------------|------|--------------------------------|----------|--------|---------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|-----------|--|----------|----------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NiIRON | NI PLATED DUCTILE IRON SERIES 400 S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Cellosolve Acetate CH ₃ COOCH ₂ CH ₂ OC ₂ H ₅ | | | | | 73 | 300 | 140 | C | C | C | C | | | B | | B | | | B | | | | | | | A | B | | | | |
| Chloral Hydrate CCl ₃ CH(OH) ₂ | All | | | | 140 | 75 | | | 70 | B to 70 | C | 550 | | | | | | | | | | | | | | | | | | | |
| Chloramine NH ₂ Cl | Dilute | | | | 73 | | | | 70 | 70 | | | | B | B | B | B | C | C | C | C | C | B | | B | B | | | | | |
| Chloric Acid HClO ₃ •7H ₂ O | 10% | | | | 140 | 140 | | | 200 | 140 | 140 | | | C | C | C | C | C | C | C | C | C | B | C | A | C | | | | | |
| Chloric Acid HClO ₃ •7H ₂ O | 20% | | | | 140 | 140 | | | | | 100 | | | C | C | C | C | C | C | C | C | C | C | C | A | C | | | | | |
| Chlorine Gas (Dry) (Moisture Content) | <150 PPM | B#* to 120 | C | B#* to 120 | 200 | 400 | C | C | C | C | 185 | C | A | C | C | C | C | B | A* | A* | B | B | A | | A | A | A | C | C | | |
| Chlorine Gas (Wet) (Moisture Content) | >150 PPM | C | B#* to 120 | C | B#* to 120 | 200 | 400 | C | C | | C | 185 | C | | C | C | C | C | C | C | C | C | C | C | C | C | A | A | A | C | C |
| Chlorine (>101 psi@ 77°F) | Liquid | C | C | C | C | 200 | | C | | B to 70 | C | B to 100 | C | | B | B | | B | C | C | C | C | C | C | C | C | C | | | | |
| Chlorinated Water | <3500 ppm | | 140 | | 140 | 210 | 400 | B to 100 | C | B to 70 | C | 185 | C | 73 | B | B | C | C | | | C | | C | B | A | A | A | A | A | C | C |
| Chlorinated Water | >3500 ppm | | C | C | C | 210 | 400 | C | C | B to 70 | C | 185 | C | 73 | C | C | C | C | | | C | | C | A | B | A | B | A | C | C | |
| Chloroacetic Acid CH ₂ ClCOOH | 50% | | | | 140 | C | 200 | 70 | C | 200 | C | C | | C | C | C | C | C | C | C | C | C | C | C | C | B | B | | C | C | |
| Chloroacetyl Chloride CICH ₂ COCl | | | | | | 73 | 125 | | | | | | | | | | | | | | | | | | | | | | | | |
| Chlorobenzene C ₆ H ₅ Cl | Dry | | | | 73 | C | 170 | 200 | C | C | C | 70 | C | A | A | A | A | C | C | B | | C | A | A | A | A | A | A | | | |
| Chlorobenzyl Chloride CIC ₆ H ₄ CH ₂ Cl | | | | | | C | 125 | | | | | | | | | | | | | | | | | | A | A | | | | | |
| Chloroform CHCl ₃ | Dry | C | C | C | 125 | 200 | C | C | C | C | 70 | 275 | A | A | A | A | A | C | C | C | C | C | A | A | A | A | A | A | | | |
| Chloropicrin CCl ₃ NO ₂ | | | | | | C | 150 | | | | | | | | | | | | | | | | | | | | | | | | |
| Chlorosulfonic Acid CISO ₂ OH | | | | | C | 73 | C | 200 | C | C | C | C | | C | C | C | C | B | B | C | C | C | B | C | C | C | B | A | A | C | C |
| Chromic Acid H ₂ CrO ₄ | 10% | C | 180 | 150 | 140 | 175 | 350 | 70 | C | 140 | C | 140 | | C | C | C | C | C | C | C | C | C | B to 212 | A to 70 | | A to 125 | B | A | A | C | C |
| Chromic Acid H ₂ CrO ₄ | 30% | C | 180 | 150 | 140 | 175 | 350 | C | C | 140 | C | 140 | | C | C | C | C | C | C | C | C | C | B to 212 | B to 70 | | A to 125 | C | | A | C | C |
| Chromic Acid H ₂ CrO ₄ | 40% | C | 180 | 150 | 140 | 175 | 300 | C | C | 140 | C | 140 | | C | C | C | C | C | C | C | C | C | B to 70 | | | C | A | C | C | | |
| Chromic Acid H ₂ CrO ₄ | 50% | C | 140 | C | 75 | 125 | 200 | C | C | 140 | C | 140 | C | C | C | C | C | C | C | C | C | C | B to 70 | | B to 212 | C | B | C | C | | |
| Chromium Potassium Sulfate CrK(SO ₄) ₂ •12H ₂ O | | | | | 73 | 140 | 73 | 200 | | 140 | 180 | 200 | 160 | 200 | A | | | | C | | | | B | B | A | B | | | | | |
| Citric Acid C ₆ H ₈ O ₇ | Sat'd | | 185 | 180 | 140 | 275 | 200 | 210 | 70 | 140 | 140 | 200 | 550 | A | C | C | C | C | C | C | C | C | B | A | A | A | A | A | C | | |
| Coconut Oil | | | | | 73 | 140 | 280 | 400 | C | 70 | B to 140 | 100 | 185 | 550 | | B | B | B | B | C | C | B | | C | B | A | | A | B | | |
| Coffee | | | | | | | | | 140 | 100 | | | 200 | | A | A | A | A | C | C | C | | A | A | A | A | A | A | A | | |

Vacuum service only. Pressure service (greater than 7 psi) causes severe chemical attack.

* Ratings are for body material only.

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|---------|----------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Coke Oven Gas | | | | 73 | 140 | 230 | 400 | 70 | B to 70 | 140 | | 185 | | | B | B | B | B | B | A | A | A | A | A | A | B | | | | | | |
| Copper Acetate Cu(C ₂ H ₃ O ₂) ₂ •H ₂ O | Sat'd. | 73 | 73 | 73 | 250 | 350 | 100 | 180 | C | 160 | 140 | | | | C | C | C | C | C | C | C | C | C | C | B | A | A | B | A | | | |
| Copper Carbonate CuCO ₃ | Sat'd. | | | 140 | 280 | 350 | 210 | | | | | 185 | | | | | | | | | | | | | B | A | A | A | | | | |
| Copper Chloride CuCl ₂ | Sat'd. | 185 | | 140 | 280 | 350 | 210 | 180 | 200 | 160 | 200 | | | A | C | C | C | C | C | C | C | C | C | B | A | A | B | A | C | C | | |
| Copper Cyanide Cu(CN) ₂ | | 185 | | 140 | 275 | 350 | 210 | 180 | | 160 | 185 | | | | C | C | C | C | C | C | C | A | C | B | A | A | B | | | C | | |
| Copper Fluoride CuF ₂ •H ₂ O | 2% | | | 140 | 280 | | 210 | B to 70 | 140 | 140 | 185 | | | A | | | | | | | | | | | | | | | | | | |
| Copper Nitrate Cu(NO ₃) ₂ •H ₂ O | 30% | | | 140 | 280 | | 210 | B to 70 | 200 | 160 | 200 | | | A | C | C | C | C | C | C | C | C | C | B | A | A | C | A | C | C | | |
| Copper Sulfate CuSO ₄ •5H ₂ O | Sat'd. | 185 | 120 | 140 | 280 | | 210 | 180 | 200 | 160 | 200 | | | A | C | C | C | C | C | C | C | C | C | C | A | A | A | A | C | A | C | |
| Corn Oil | | C | 73 | 73 | 275 | 400 | C | 180 | C | C | 300 | | | | B | B | B | B | B | B | B | B | B | B | A | A | A | A | B | | A | |
| Corn Syrup | | | 150 | 140 | 250 | | | 100 | 200 | 100 | 185 | | | | | | | | | | | | | | | | | | | | | |
| Cottonseed Oil | | 185 | 150 | 140 | 280 | 400 | C | 180 | 200 | | 185 | 275 | | | B | B | B | B | B | B | B | B | B | B | A | A | A | A | B | | A | |
| Creosote | | 73 | 73 | | 350 | C | 73 | 73 | C | 73 | 275 | | | B | B | B | B | B | A | A | A | A | A | A | A | A | A | A | A | B | | |
| Cresol CH ₃ C ₆ H ₄ OH | 90% | | 73 | C | 150 | 200 | C | C | B to 140 | C | 100 | C | | | | | | | | | | | | | | B | | B | | | | |
| Cresylic Acid C ₇ H ₈ O | 50% | | | 140 | 150 | 200 | C | C | C | C | 185 | 275 | | | A | A | A | A | A | A | B | A | A | A | A | A | A | A | A | A | A | |
| Croton Aldehyde CH ₃ CH:CHCHO | | | | C | 125 | 200 | | C | | 70 | C | | | | | | | | | | | | | | | | | | | | | |
| Crude Oil | | 185 | | 140 | 280 | 400 | C | 70 | | | 200 | 275 | | | C | C | C | C | C | C | C | B | | | A | A | A | A | B | | C | |
| Cumene C ₆ H ₅ CH(CH ₃) ₂ | | | | | 100 | 300 | C | C | C | C | 200 | | | | | | | | | | | B | | | B | B | | A | | | | |
| Cupric Fluoride CuF ₂ | | | | | 140 | 280 | | 210 | | | | | A | | | | | | | | | | | | | | | | | | | |
| Cuproic Sulfate CuSO ₄ •5H ₂ O | Sat'd. | 100 | | 73 | 140 | 280 | 250 | 210 | 180 | 140 | 160 | 200 | 550 | A | | | | | | | | | | | | | | | | | | |
| Cuprous Chloride CuCl | Sat'd. | 70 | | | 140 | 250 | 350 | 200 | 180 | 70 | 70 | 200 | | | A | C | | C | | | | | | | | | | | | | C | |
| Cyclohexane C ₆ H ₁₂ | | 100 | C | C | C | 280 | 300 | C | C | C | C | 185 | 550 | | | A | A | A | A | B | B | A | | B | A | A | A | A | A | A | | |
| Cyclohexanol C ₆ H ₁₁ OH | | 100 | C | 120 | C | 150 | 250 | C | C | C | C | 185 | 550 | | | | | | | A | A | | | A | A | A | A | A | | | | |
| Cyclohexanone C ₆ H ₁₀ O | | | C | C | C | 73 | 200 | 70 | C | C | C | C | 275 | | B | B | B | B | B | B | B | B | | B | B | A | A | B | A | | | |
| Decahydronaphthalene C ₁₀ H ₁₈ | | | | | | 400 | C | C | C | C | 200 | | | | | | | | | | | | | | | | | | | | | |
| Detergents (Heavy Duty) | | C | C | 150 | C | | | 250 | 180 | 200 | 160 | 210 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Dextrin (Starch Gum) | Sat'd. | | | | 140 | 250 | 200 | C | 180 | | 200 | | | A | A | A | A | B | B | B | B | | | A | | A | | | | A | | |
| Dextrose C ₆ H ₁₂ O ₆ | | | | | 140 | 275 | 400 | 140 | 180 | 140 | 160 | 200 | | | A | | | | | | | | | A | | A | | | | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|----------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------|----------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROXYL | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE SS. | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Diacetone Alcohol <chem>CH3COCH2C(CH3)OH</chem> | | C | 120 | C | 70 | 350 | 70 | C | | C | C | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Dibutoxyethyl Phthalate <chem>C20H30O6</chem> | | | | C | | | B to 70 | C | 140 | C | 200 | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| n-Diethyl Ether <chem>C4H9OC4H9</chem> | | | | | 100 | 350 | C | C | C | C | C | | | | | | | | | | | | | | | | | | | |
| Diethyl Phthalate <chem>C6H4(COOC4H9)2</chem> | | | | 120 | C | C | 350 | 70 | C | C | C | C | 275 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Dibutyl Sebacate <chem>C4H9OCO(CH2)2OCOC4H9</chem> | | | | | 73 | C | 350 | 70 | C | C | C | C | | | | | | | | | | | | | | | | | | |
| Dichlorobenzene <chem>C6H4Cl2</chem> | | | | C | 150 | | C | C | C | C | 150 | C | | | | | | | | | | | | | | | | | | |
| Dichloroethylene <chem>C2H2Cl2</chem> | | | C | C | 225 | 350 | C | C | C | C | 185 | | | | | | | B | | B | | | | B | | | | | | |
| Diesel Fuels | | | | | 140 | 280 | 350 | C | 70 | C | C | 185 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Diethylamine <chem>C4H10NH</chem> | | | | | C | 73 | 200 | 70 | 70 | | C | | | A | C | C | C | C | A | A | C | | | A | A | A | A | B | C | |
| Diethyl Cellosolve <chem>C6H14O2</chem> | | | | | | 280 | | C | 140 | | 100 | 200 | | | | | | | | | | | | A | A | | A | A | | |
| Diethyl Ether <chem>C4H10O</chem> | | | 73 | 73 | 73 | | C | | | C | 275 | A | | | | | | | | | | | | | | | | | | |
| Diglycolic Acid <chem>O(CH2COOH)2</chem> | Sat'd. | | | | 140 | 73 | 250 | 70 | 70 | | 70 | | | | | | | | | | | | | | | | | | | |
| Dimethylamine <chem>(CH3)2NH</chem> | | | | | 120 | 140 | 75 | | 140 | C | C | C | | | | | | | | | | | | | | | | | | |
| Dimethyl Formamide <chem>HCON(CH3)2</chem> | | C | 120 | C | C | 250 | C | 100 | 100 | C | C | 275 | | | B | B | B | B | B | B | B | | | | A | | A | A | | |
| Dimethylhydrazine <chem>(CH3)2NNH2</chem> | | | | | C | C | | | | C | | | C | | | | | | | | | | | | | | | | | |
| Dinonyl Phthalate <chem>C6H4(COOC8H17)2</chem> | | | | | | 32 | B to 10 | C | C | C | B to 10 | | | | | | | | | | | | | | | | | | | |
| Diocetyl Phthalate <chem>C6H4(COOC8H17)2</chem> | | C | C | C | 75 | 200 | 70 | | C | C | 70 | 275 | | | A | A | A | A | A | C | C | C | | | | | | | | |
| Dioxane <chem>O:(CH2)4:O</chem> | | C | 73 | C | C | | | 70 | C | C | C | 275 | A | A | A | A | A | A | A | A | A | | | | A | A | A | | | |
| Diphenyl Oxide <chem>(C6H5)2O</chem> | Sat'd. | | | | | 125 | | C | C | | C | 300 | C | | A | A | A | A | A | | | | | | | | | | | A |
| Disodium Phosphate <chem>Na2HPO4</chem> | | | 185 | | 140 | 200 | 400 | 210 | 100 | 140 | | | | | A | B | B | B | B | B | B | | | | A | | A | B | | |
| Dow Therm A <chem>C12H10•C12H10O</chem> | | | | C | | 212 | C | C | C | C | C | C | A | A | A | A | A | B | A | A | | A | A | A | A | A | A | A | A | |
| Ether <chem>C4H10O</chem> | | C | 73 | C | 125 | | | C | C | C | C | | | A | A | A | | | B | B | B | A | A | A | A | A | A | A | A | A |
| Ethyl Acetate <chem>CH3COOC2H5</chem> | | C | 120 | C | C | 200 | 70 | C | C | C | C | 550 | | A | A | B | | | A | A | A | | | | A | A | A | A | B | A |
| Ethyl Acetoacetate <chem>CH3COCH2COOC2H5</chem> | | C | | C | 73 | 200 | 100 | C | | | C | | | | | | | | | | | | | | | | | | | |
| Ethyl Acrylate <chem>CH2=CHCOOC2H5</chem> | | C | | C | 73 | 350 | 70 | C | C | C | C | | | A | A | | | | A | A | A | | A | A | A | A | A | A | A | |
| Ethyl Alcohol (Ethenol) <chem>C2H5OH</chem> | | | 140 | 180 | 140 | 280 | 300 | 170 | 180 | 200 | 70 | | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | |
|--|---------------|------------------------------------|------|-----|-----|------|-----------------------------------|---------|--------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|-------------------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Ethyl Benzene <chem>C6H5C2H5</chem> | | | | C | C | 125 | 350 | C | C | C | C | 70 | | | | | | | B | B | | | | | | A | A | A | A | A |
| Ethyl Chloride <chem>C2H5Cl</chem> | Dry | | | 73 | C | 280 | 350 | B to 70 | C | 70 | B to 70 | 140 | 550 | A | | | | | A | A | A | A | A | A | A | A | A | B | A | |
| Ethyl Chloroacetate <chem>CH3ClCOOC2H5</chem> | | | | C | 75 | | | | | | | | | | | | | | | | | | | | | | | | | |
| Ethylene Bromide <chem>BrCH2CH2Br</chem> | Dry | C | C | C | C | 280 | 350 | C | C | | C | B to 70 | | | A | | | | A | A | | | | | A | A | A | A | A | |
| Ethylene Chloride <chem>CICH2CH2Cl</chem> | Dry | C | | 73 | C | 280 | 350 | | C | C | | 70 | | | | | | | | | | | | | A | | A | A | | |
| Ethylene Chlorohydrin <chem>CICH2CH2OH</chem> | | | | 73 | C | 73 | 200 | 70 | C | 70 | 70 | C | | A | | | | | | | | | A | | | | | | | |
| Ethylene Diamine <chem>NH2CH2CH2NH2</chem> | | C | | 120 | C | 225 | | 70 | 100 | 100 | 100 | | | | A | C | | A | A | B | | | | A | A | B | | A | | |
| Ethylene Dichloride <chem>C2H4Cl2</chem> | Dry | C | | 73 | C | 280 | 350 | C | C | C | C | 120 | 275 | A | A | A | | A | A | A | A | | A | A | A | A | A | A | | |
| Ethylene Glycol <chem>CH2OHCH2OC</chem> | | 73 | 185 | 120 | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 250 | 550 | A | A | A | A | A | A | A | A | | A | A | A | A | A | A | | |
| Ethylene Oxide <chem>CH2CH2O</chem> | | | C | C | C | 400 | C | C | C | C | C | 275 | | A | A | | | B | A | A | | A | | A | | A | B | A | | |
| Ethyl Ether <chem>(C2H5)2O</chem> | | | C | C | 125 | 250 | C | C | C | C | C | 275 | | | | | | | | | | | | | | | | | | |
| Ethyl Formate <chem>HCOOC2H5</chem> | | | | | | 73 | | C | | 70 | C | | | A | A | | | A | A | | | | A | A | | A | | | | |
| 2-Ethyhexanol <chem>CH3(CH2)2CHC2H5CH2OH</chem> | | | | | | 250 | | | | 70 | C | | | | | | | | | | | | | | | | | | | |
| Ethyl Mercaptan <chem>C2H5SH</chem> | | | | | | 75 | | | C | | | | | A | | | | | | | | | | | A | | A | A | | |
| Ethyl Oxalate <chem>(COOC2H5)2</chem> | | | | | | | 140 | C | | C | | | | | | | | | | | | | | | | | | | | |
| Fatty Acids <chem>R-COOH</chem> | | 73 | 120 | 140 | 280 | 400 | C | 140 | C | 140 | C | 185 | 275 | A | C | C | C | C | C | C | C | C | C | A | A | A | A | C | | |
| Ferric Chloride (Aqueous) <chem>FeCl3</chem> | Sat'd | 185 | 180 | 140 | 280 | 400 | 225 | 180 | 200 | 160 | 200 | 550 | A | C | C | C | C | C | C | C | C | C | C | C | C | C | A to 175 | C | | |
| Ferric Hydroxide <chem>Fe(OH)3</chem> | Sat'd | 185 | 180 | 140 | 250 | 400 | 180 | 100 | 100 | 100 | 180 | | | | | | | C | C | | | C | | A | | A | A | C | | |
| Ferric Nitrate <chem>Fe(NO3)3•5H2O</chem> | Sat'd | 185 | 180 | 140 | 280 | 400 | 210 | 180 | 140 | 160 | 200 | | | A | C | C | C | C | C | C | C | C | B | A | A | A | C | A | | |
| Ferric Sulfate <chem>Fe2(SO4)3</chem> | | | | 180 | 140 | 280 | 200 | 210 | 140 | 140 | 140 | 185 | 550 | A | C | C | C | C | C | C | C | C | C | B | A | A | A | C | | |
| Ferrous Chloride <chem>FeCl2</chem> | Sat'd | 185 | 180 | 140 | 280 | 400 | 200 | 200 | 180 | | | 200 | 275 | A | C | C | C | C | C | C | C | C | C | C | C | C | C | B | | |
| Ferrous Hydroxide <chem>Fe(OH)2</chem> | Sat'd | 185 | 180 | 73 | 250 | 400 | 180 | 180 | | | 180 | | | | | | | C | | | | | | A | | | | C | | |
| Ferrous Nitrate <chem>Fe(NO3)2</chem> | | 140 | 140 | 73 | 280 | 400 | 180 | 180 | 140 | 160 | 200 | | | A | | | | | | | | | | | | | | A | A | |
| Ferrous Sulfate <chem>FeSO4</chem> | | 70 | 185 | 180 | 140 | 280 | 400 | 200 | 180 | 140 | 160 | 200 | | A | C | C | B | | C | C | C | C | C | A | A | A | A | A | | |
| Fish Oil | | | | | 140 | | 300 | C | 70 | C | | 70 | | | A | A | C | | B | A | A | | A | A | A | A | A | A | | |
| Flue Gas | | | | | | | C | 180 | | | 300 | | | A | A | | | A | A | A | | A | A | A | A | A | A | A | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|---------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (65% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Fluoboric Acid HBF ₄ | | 73 | 73 | 140 | 275 | 350 | 140 | 160 | 140 | 160 | 160 | 140 | | B | B | | | C | C | | | A | | A | | | C | C | | | |
| Fluorine Gas (Dry) F ₂ | 100% | C | 73 | C | 73 | 73 | C | C | C | 140 | C | C | C | B to 300 | B | B | | C | C | A | | | A | A | A | A | A | | | | |
| Fluorine Gas (Wet) F ₂ | | C | C | 73 | 73 | C | C | | | | 100 | C | C | C | C | C | C | C | C | C | | | A | A | A | A | | | | | |
| Fluosilicic Acid H ₂ SIF ₆ | | See Hydrofluosilicic Acid | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Formaldehyde HCHO | Dilute | | | 120 | 140 | 125 | 300 | 140 | C | 200 | 140 | C | 550 | A | A | A | B | C | C | B | | A | A | A | A | A | A | | | | |
| Formaldehyde HCHO | 35% | | 73 | 180 | 140 | 125 | 300 | 140 | C | 150 | 140 | C | 550 | A | A | A | B | C | | B | | A | A | A | A | A | A | | | | |
| Formaldehyde HCHO | 37% | | 73 | 180 | 140 | 125 | 300 | 140 | C | C | 100 | C | 550 | A | A | A | B | C | | B | | A | A | A | A | A | A | | | | |
| Formaldehyde HCHO | 50% | | | 140 | | 300 | 140 | C | C | 140 | C | 275 | A | B | B | B | C | | B | | B | A | A | A | A | A | A | | | | |
| Formic Acid HCOOH | | | 73 | 73 | 73 | 250 | 300 | 200 | C | 70 | 140 | C | 275 | A | C | C | B | C | C | C | B | C | A | A | A | A | A | A | | | |
| Formic Acid Anhydrous HCOOH | | | 73 | 180 | | | | | C | 160 | 100 | C | | | | | | | | | | | A | A | A | | | | | | |
| Freon 11 CCl ₃ F | 100% | C | 73 | | 140 | 200 | 300 | C | 70 | 130 | C | 70 | C | A | A | A | A | A | A | B | B | B | B | A | A | A | A | A | A | | |
| Freon 12 CCl ₂ F ₂ | 100% | | 73 | 73 | 140 | 200 | C | C | | 130 | 130 | C | 550 | A | A | A | A | A | A | B | B | B | B | A | A | A | A | A | A | | |
| Freon 21 CHCl ₂ F | 100% | | | | C | 200 | 300 | C | C | | C | C | | A | A | A | A | A | A | B | B | B | B | A | A | A | A | A | A | | |
| Freon 22 CHClF ₂ | 100% | | 73 | C | 200 | C | C | C | 130 | 130 | C | 275 | A | A | A | A | A | A | B | B | B | B | B | A | A | A | A | A | A | | |
| Freon 113 C ₂ Cl ₃ F ₃ | 100% | | | | 140 | 200 | 300 | C | 130 | 130 | 130 | 130 | | A | A | A | A | A | A | B | B | B | B | B | A | A | A | A | A | A | |
| Freon 114 C ₂ Cl ₂ F ₄ | 100% | | | | 140 | 200 | 300 | C | 130 | 70 | 70 | C | 275 | A | A | A | A | A | A | B | B | B | B | B | A | A | A | A | A | A | |
| Fructose C ₆ H ₁₂ O ₆ | | | 185 | | 140 | 280 | 300 | 175 | 140 | 140 | 160 | 225 | | | | | | | | | | | A | A | | | A | A | A | A | A |
| Furfural C ₄ H ₈ OCHO | | | | C | C | 75 | 300 | 140 | C | 70 | 70 | C | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Gallic Acid C ₆ H ₂ (OH) ₃ CO ₂ H | | | 73 | | 140 | 75 | 300 | 70 | C | 70 | 70 | 185 | | | B | B | C | | C | C | C | C | A | A | A | A | A | A | A | A | |
| Gasoline, Leaded | | C | C | C | C | 275 | 200 | C | 70 | 70 | 70 | 100 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Gasoline, Unleaded | | C | C | C | C | 275 | 200 | C | 70 | 70 | | 100 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Gasohol | | C | C | C | C | 280 | 200 | C | 70 | | | 100 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Gasoline, Sour | | C | C | C | C | 280 | 200 | C | 70 | | | 100 | | A | B | B | | A | A | A | A | A | B | A | A | A | C | A | | | |
| Gelatin | | 150 | 180 | 140 | 250 | 300 | 200 | 180 | 200 | 160 | 250 | | | C | C | B | | C | C | C | C | C | C | C | A | A | A | A | | | |
| Glauber's Salt Na ₂ SO ₄ •10H ₂ O | | | | | | 200 | 70 | C | 100 | 160 | 200 | | | A | A | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Glucose C ₆ H ₁₂ O ₆ •H ₂ O | | 180 | 185 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | 300 | 275 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Glue | | | | | | 250 | 400 | 100 | 140 | 200 | 160 | 250 | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | |
|---|---------------|-----------------------------------|------|-----|-----|------|--------------------------------|------|---------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|------------------------------|------------------|----------|---------|----------|-------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE IRON SS.3. | 400 SERIES SS.3. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Glycerin C ₃ H ₅ (OH) ₃ | | 140 | 185 | 180 | 140 | 280 | 400 | 200 | 70 | 200 | 160 | 300 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Glycol | | See Ethylene and Propylene Glycol | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Glycol Amine | | | | | | | | | | | | | | C | C | C | | A | A | A | | A | | A | | A | | | | | |
| Glycolic Acid OHCH ₂ COOH | Sat'd. | | 73 | 140 | 73 | 200 | | C | C | 70 | C | 550 | | B | B | | C | C | C | | C | A | A | B | | | | | | | |
| Glyoxal CHOCHO | | | | | | | | C | C | 70 | | | | B | B | B | | C | C | C | | C | A | A | A | B | | | | | |
| Grape Sugar C ₆ H ₁₂ O ₆ | | | 140 | | | 250 | 180 | 200 | 160 | 185 | | | | | | | | | | | | | | | | | | | | | |
| Grease | | | | | | C | 150 | C | 100 | 200 | | | | C | C | C | C | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Green Liquor | | | | | | 150 | 150 | 70 | 70 | | | | | C | C | C | | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Gypsum CaSO ₄ •H ₂ O | Slurry | | | 275 | 350 | 210 | 180 | 200 | 160 | 200 | | | | A | A | B | B | A | A | B | A | A | A | A | A | A | A | A | A | A | |
| Heptane C ₇ H ₁₆ | | C | 140 | 280 | 300 | C | 70 | 70 | 70 | 185 | 550 | | | A | A | A | | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| n-Hexane C ₆ H ₁₄ | C | 73 | 73 | 73 | 280 | 300 | C | 70 | 70 | 70 | 70 | 550 | | A | A | A | | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Hexanol CH ₃ (CH ₂) ₄ CH ₂ OH | | | 100 | 175 | 300 | C | 70 | 70 | B to 70 | 160 | | | | A | A | A | | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Hydraulic Oil (Petroleum) | | | | 73 | | 300 | C | C | 70 | 70 | 250 | 550 | A | A | A | B | | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Hydrazine H ₂ NNH ₂ | | | C | 200 | 250 | 70 | 70 | 70 | | C | C | A | C | C | C | C | C | C | C | C | C | A | A | A | | | | | | | |
| Hydrobromic Acid HBr | 20% | 73 | 120 | 140 | 280 | 250 | 140 | C | 100 | B to 70 | 185 | C | A | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | | |
| Hydrobromic Acid HBr | 50% | | 140 | 140 | 280 | 250 | 140 | C | 100 | B to 70 | 185 | C | A | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | | |
| Hydrochloric Acid HCl | <25% | C | 180 | 150 | 140 | 280 | 250 | 150 | C | 100 | | 100 | 275 | A | C | C | C | C | C | C | C | C | C | C | B | C | B | C | C | C | |
| Hydrochloric Acid HCl (Muriatic Acid) | 37% | C | 160 | 150 | 140 | 280 | 250 | 150 | C | 100 | | 100 | | C | C | C | C | C | C | C | C | C | C | B | C | B | C | C | C | C | |
| Hydrocyanic Acid HCN | 10% | | 73 | 140 | 280 | 250 | 200 | 70 | 200 | | 185 | 275 | | C | C | C | C | C | C | C | C | C | C | A | B | A | A | C | A | C | |
| Hydrofluoric Acid HF | <3% | 125 | 73 | 180 | 73 | 250 | 300 | C | C | 150 | 70 | 150 | C | A | C | C | C | C | C | C | C | C | C | C | C | B | A | C | A | C | |
| Hydrofluoric Acid HF | 30% | C | C | 140 | 73 | 250 | 300 | C | C | 150 | 70 | 150 | C | A | C | C | C | C | C | C | C | C | C | C | C | B | A | C | A | C | |
| Hydrofluoric Acid HF | 40% | C | C | 140 | 73 | 250 | 300 | C | C | 140 | C | 100 | C | A | C | C | C | C | C | C | C | C | C | C | C | A | B | B | C | A | C |
| Hydrofluoric Acid HF | 50% | C | C | 100 | 73 | 200 | 300 | C | C | 140 | C | 75 | C | A | C | C | C | C | C | C | C | C | C | C | C | C | B | B | C | A | C |
| Hydrofluosilicic Acid H ₂ SiF ₆ | 50% | | 140 | 140 | 140 | 280 | 300 | 140 | 170 | 150 | | 200 | | C | B | B | | C | C | C | | C | B | B | B | A | A | | C | C | |
| Hydrogen H ₂ | Gas | | 73 | 73 | 140 | 280 | 300 | 250 | 180 | 200 | 160 | 300 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|---------|----------|--------------|---------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-------------------|-----------------|----------|---------|----------|-------|----------|-------------|----------|--------|--|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (65% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE | 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER | |
| Hydrogen Cyanide HCN | | | | 140 | 280 | | | 70 | 100 | 70 | | 275 | | | | | | | | | | | | | A | | | | | | | | |
| Hydrogen Fluoride Anhydrous HF | | | C | 73 | C | 200 | 250 | 70 | C | | C | C | A | | | | | | | | | | | A | A | A | | A | | | | | |
| Hydrogen Peroxide H ₂ O ₂ | 50% | 185 | 150 | 140 | 150 | 300 | 100 | C | 200 | C | 185 | 275 | A | C | C | C | C | C | C | C | B | C | C | A | A | A | A | A | C | C | | | |
| Hydrogen Peroxide H ₂ O ₂ | 90% | | | 140 | 73 | 30 | C | C | 200 | C | 100 | 250 | C | C | C | C | C | C | C | C | B | C | C | A | A | A | A | B | B | C | C | | |
| Hydrogen Phosphide PH ₃ | | | | 140 | 150 | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Hydrogen Sulfide H ₂ S | Dry | 185 | 150 | 140 | 280 | | 100 | C | 140 | C | 140 | | A | B | | | | | | | B | B | | | A | B | A | A | A | A | B | | |
| Hydrogen Sulfide H ₂ S | Wet | | | 140 | 225 | | 100 | C | 70 | C | 140 | 550 | A | C | C | C | C | C | C | C | C | C | C | A | C | A | B | B | C | C | | | |
| Hydrogen Sulfite H ₂ SO ₃ | | | | | | | 70 | C | 70 | | 100 | | C | C | C | C | C | C | C | C | C | C | C | A | A | A | A | A | C | | | | |
| Hydroquinone C ₆ H ₄ (OH) ₂ | Sat'd. | | | 140 | 250 | 300 | C | 70 | | C | 185 | 275 | | | | | | | | | | | | A | | A | A | | | | | | |
| Hydroxylamine sulfate (NH ₂ OH) ₂ ·H ₂ SO ₄ | | | | 140 | | 70 | | | 70 | | | | | | | | | | | | | | | | | | | | | | | | |
| Hypochlorous Acid HOCl | 10% | B | 73 | 140 | 70 | 300 | 70 | C | | | 70 | | | | | | | | | | | | | | | | | | | | C | | |
| Inks | | | | | | 300 | | 70 | | 70 | 70 | | | A | A | A | | C | C | C | C | C | C | A | A | A | A | A | | | | | |
| Iodine I ₂ | 10% | 73 | 150 | | 150 | 200 | 70 | 70 | 70 | C | 70 | 275 | B to 70 | C | C | C | C | C | C | C | C | C | C | C | C | B | A | A | A | C | | | |
| Iron Phosphate FeH ₃ PO ₄ | | | | | | | | | | | 180 | | A | C | C | C | C | | | | | | | B | A | A | A | A | C | | C | | |
| Isobutane (CH ₃) ₂ CHCH ₃ | | | | | | 140 | C | 70 | C | C | B to 70 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Isobutyl Alcohol (CH ₃) ₂ CHCH ₂ OH | | | | | | 250 | 300 | 140 | 70 | 70 | 70 | 140 | | | | | | | | | | | | | A | A | | | | | | | |
| Iooctane (CH ₃) ₃ CCH ₂ CH(CH ₃) ₂ | | | 73 | | 250 | 300 | C | 70 | 200 | 70 | 185 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Isophorone C(O)CHC(CH ₃)CH ₂ (CH ₃) ₂ CH ₂ | | | | | | 175 | | C | C | | C | | | | | | | | | | | | | | | | | | | | | | |
| Isopropyl Acetate CH ₃ COCOCH(CH ₃) ₂ | C | | | | | 200 | 70 | C | C | C | C | 550 | A | A | | | | | | | A | A | A | A | A | A | A | A | A | A | A | A | |
| Isopropyl Alcohol (CH ₃) ₂ CHOH | C | B to 70 | 180 | 140 | 140 | 300 | 140 | 70 | 200 | 70 | 160 | A | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Isopropyl Chloride CH ₃ CHClCH ₃ | | | | | | 100 | 200 | C | C | | C | 70 | | | | | | | | | | | | | | | | | | | | | |
| Isopropyl Ether (CH ₃) ₂ COCH(CH ₃) ₂ | | C | | C | 125 | 140 | C | 70 | C | C | C | 550 | | A | A | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| JP-3 Fuel | | C | | C | | 200 | C | 70 | C | C | 185 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| JP-4 Fuel | | C | | C | 200 | 300 | C | 70 | C | C | 300 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| JP-5 Fuel | | C | | C | 200 | 300 | C | 70 | C | C | 300 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| JP-6 Fuel | | C | | C | 200 | | C | 100 | C | C | 100 | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| JP-8 Fuel | | C | | C | | C | C | C | C | C | 150 | | | | | | | | | | | | | | | | | | | | | | |
| Kelp Slurry | | | | | | | C | 70 | C | | 100 | | | B | B | B | B | B | B | B | B | B | B | B | A | A | A | A | A | A | A | | |

* Ratings are for body material only.

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|---------|---------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|------------------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Kerosene | | C | 185 | 73 | 140 | 280 | 250 | C | 140 | C | 70 | 300 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Ketchup | | | | 73 | | | 250 | 210 | 140 | B to 70 | | 200 | | | C | C | C | | C | C | C | | C | B | A | A | A | A | C | |
| Ketones | | C | C | | C | C | 200 | C | C | C | C | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Kraft Liquors | | 100 | 185 | | 140 | | 250 | | 70 | 70 | 70 | 100 | | | C | C | C | C | C | C | C | | C | A | | A | | | | |
| Lactic Acid CH ₃ CHOHCOOH | 25% | | | 150 | 140 | 125 | 300 | 70 | | 140 | 140 | 70 | 550 | A | C | C | C | C | C | B | C | | B | A | A | A | A | A | A | |
| Lactic Acid CH ₃ CHOHCOOH | 80% | | | 150 | 73 | 125 | 300 | 70 | C | 140 | | 70 | 550 | A | C | C | C | C | C | B | C | | B | A | A | A | A | A | A | |
| Lard Oil | | | 185 | 73 | 140 | 280 | 300 | C | 140 | C | 70 | 185 | | | C | C | C | C | B | B | B | | B | A | | A | B | | C | |
| Latex (C ₂ H ₆ OSi)x | | | | | | 200 | 70 | 70 | | 100 | 70 | | | A | A | | | A | A | | | A | A | A | A | A | | | | |
| Lauric Acid CH ₃ (CH ₂) ₁₀ COOH | | | | | 140 | 225 | 300 | | 70 | | | 100 | | | | | | C | C | | | C | A | A | | | | | | |
| Lauryl Chloride C ₁₂ H ₂₅ Cl | | | | | | | 300 | 140 | 70 | | | 200 | | | | | C | C | | | C | A | A | A | | | | | | |
| Lead Acetate Pb(C ₂ H ₃ O ₂) ₂ •H ₂ O | Sat'd. | 185 | 180 | 140 | 280 | 300 | 210 | 70 | 100 | 160 | C | 275 | | | C | C | | C | C | C | | C | A | A | A | A | A | | | |
| Lead Chloride PbCl ₂ | | | | 73 | 140 | 250 | 300 | C | 100 | 100 | 70 | 140 | | A | | | | | | | | | | | | | | | | |
| Lead Nitrate Pb(NO ₃) ₂ | Sat'd. | 185 | 180 | 140 | 250 | 300 | 175 | 180 | | 140 | 225 | 275 | A | | | | | | | | | | | A | A | A | A | A | | |
| Lead Sulfate PbSO ₄ | | | | 185 | 150 | 140 | 250 | 300 | 210 | 180 | 200 | 140 | 225 | | A | B | B | | C | C | C | | C | B | B | B | B | B | | |
| Lemon Oil | | | C | | 250 | 300 | | | 140 | 100 | 200 | | | | | C | C | | | C | B | A | A | A | A | | | | | |
| Ligroin | | | | | | | | 100 | C | 70 | 100 | | | | A | A | | | | | | | | | | | | | | |
| Lime Slurry CaO | | | | | | | | 100 | 100 | 160 | 100 | | | | A | A | | | | | | | | | A | A | A | A | A | |
| Lime Sulfur (CaS)x | | | | 73 | 140 | | | 210 | C | 160 | 100 | 185 | | | C | C | C | C | A | A | A | | A | A | A | A | A | | | |
| Linoleic Acid CH ₃ (CH ₂) ₄ HC:CHCH ₂ CH:CH(CH ₂) ₄ COOH | | | | | 140 | 250 | 300 | C | B to 70 | C | | 140 | 275 | | C | C | C | C | C | C | | C | C | B | B | A | A | A | C | |
| Linoleic Oil | | | | | | 140 | 230 | 300 | | | | | 70 | | | | | | | | | | | | | | | | | |
| Linseed Oil | | 100 | 185 | 150 | 140 | 280 | 300 | B to 70 | 180 | 200 | 70 | 250 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Liqueurs | | | | | | 140 | | | | 70 | 70 | | | | | | | | | | | | | | | | | | | |
| Lithium Bromide LiBr | | | | | | 140 | 225 | 300 | | 140 | | 200 | 550 | A | | | | | | | | | | | | | | | | |
| Lithium Chloride LiCl | | | | | | | 250 | | 100 | 70 | | 140 | 550 | A | B | B | B | | B | B | C | | B | A | A | A | A | | | |
| Lithium Hydroxide LiOH | | | | | | | | 100 | 70 | | 140 | | | C | C | C | C | A | A | | | A | A | A | A | B | | | | |
| Lubricating Oil (ASTM #1) | | | 73 | C | 140 | 280 | 350 | C | 180 | C | 70 | 150 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Lubricating Oil (ASTM #2) | | | 73 | C | 140 | 280 | 350 | C | 180 | C | 70 | 150 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Lubricating Oil (ASTM #3) | | | 73 | C | 140 | 280 | 350 | C | 180 | C | 70 | 150 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|----------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|--|----------|---------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROXYL | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE IRON SERIES 400 S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Ludox SiO ₂ | | | | | | | | | | | | | | | C | C | C | C | A | A | A | | A | A | A | A | | | | | |
| Magnesium Carbonate MgCO ₃ | | | | 140 | 280 | 225 | 170 | 140 | 140 | 140 | 210 | 275 | | B | B | | | B | B | B | | B | A | A | A | A | A | | | | |
| Magnesium Chloride MgCl ₂ | Sat'd. | 185 | 180 | 140 | 280 | 400 | 170 | 180 | 200 | 160 | 170 | 275 | A | A | A | B | B | C | C | C | C | C | C | C | B | A | A | A | A | | |
| Magnesium Citrate MgHC ₆ H ₅ O ₇ •H ₂ O | | | | 140 | 250 | 300 | 175 | 180 | | | | 225 | | | | | | | | | | | | | | | | | | | |
| Magnesium Fluoride MgF ₂ | | | | | | | 140 | | | | | 200 | A | | | | | | C | | | C | B | | | | | | | | |
| Magnesium Oxide MgO | | | | | | | 140 | 140 | | 160 | | | A | A | | | | A | | | A | | | | | | A | | | | |
| Magnesium Sulfate MgSO ₄ •7H ₂ O | | 185 | 180 | 140 | 280 | 300 | 175 | 180 | 140 | 160 | 200 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Maleic Acid HOOCCH:CHCOOH | Sat'd. | 185 | 180 | 140 | 250 | 250 | 70 | C | | C | 200 | 550 | A | C | C | B | C | C | C | C | C | C | B | A | B | A | B | A | B | | |
| Maleic Acid COOCHCHCH(OH)COOH | | 185 | 150 | 140 | 250 | 250 | C | 100 | 70 | 70 | 200 | | B | B | | | C | C | C | C | C | C | A | A | A | A | A | A | A | A | A |
| Manganese Sulfate MnSO ₄ •4H ₂ O | | | 150 | 140 | 250 | 300 | 175 | 140 | 180 | 160 | 225 | 225 | A | A | A | A | C | C | B | C | C | A | | | | | | | | | |
| Mercuric Chloride HgCl ₂ | | 140 | 180 | 140 | 250 | 300 | 210 | 140 | 140 | 140 | 185 | 550 | A | C | C | C | C | C | C | C | C | C | C | C | C | B | C | A | C | C | |
| Mercuric Cyanide Hg(CN) ₂ | Satd. | | | 140 | 250 | 300 | 70 | 70 | 140 | 70 | 70 | 275 | | C | C | C | C | C | C | C | C | C | C | A | | A | C | | | C | |
| Mercuric Sulfate HgSO ₄ | Sat'd. | | | 140 | 230 | 300 | 70 | 70 | | | 70 | | A | C | C | C | C | | | | | | | | | | | | | C | |
| Mercurous Nitrate HgNO ₃ •2H ₂ O | Sat'd. | | | 140 | 230 | 300 | 70 | C | | C | 70 | 275 | A | C | C | C | C | C | C | C | C | C | A | A | A | A | A | C | C | | |
| Mercury Hg | | 185 | 150 | 140 | 275 | 300 | 210 | 140 | 140 | 140 | 185 | 550 | A | C | C | C | C | A | A | A | A | A | A | A | A | A | B | A | C | | |
| Methane CH ₄ | C | | | 140 | 275 | 300 | C | 180 | 70 | 70 | 185 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Methanol (Methyl Alcohol) CH ₃ OH | C | C | 180 | 140 | 280 | 300 | 140 | 140 | 140 | 140 | C | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Methoxyethyl Oleate CH ₃ OCH ₂ CH ₂ (OOCCH ₂ H ₃₃) ₂ | | | | 73 | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Methyl Acetate CH ₃ CO ₂ CH ₃ | | | | | 100 | 300 | B to 70 | C | C | C | C | 550 | | B | B | | | B | B | B | B | B | A | | A | A | A | A | A | | |
| Methyl Acetone C ₂ H ₆ O | | | | | C | | 70 | | C | C | | | | C | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Methyl Acrylate CHCO ₂ C ₂ H ₅ | Tech. Pure | | | | 100 | 300 | B to 70 | C | C | C | C | | | | C | | | | | | | | | A | | A | A | | | | |
| Methyl Amine CH ₃ NH ₂ | | C | C | C | C | 300 | 70 | | | 70 | 100 | | | C | C | | | A | A | B | | A | | A | | A | C | | | | |
| Methyl Bromide CH ₃ Br | | | | C | 280 | 300 | C | 70 | C | C | 185 | 275 | | C | C | B | | C | C | B | | | B | | B | B | | | | | |
| Methyl Cellosolve HOCH ₂ CH ₂ OCH ₃ | | | C | 280 | | 70 | C | 70 | 70 | C | | | | A | A | B | | B | B | B | | | A | A | A | A | A | A | A | A | |
| Methyl Chloride CH ₃ Cl | Dry | C | | C | 280 | 250 | C | C | C | C | 70 | | | A | A | C | C | A | A | A | A | A | A | A | A | A | A | A | C | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------|----------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE SS. | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Methyl Chloroform CH ₃ CCl | | C | C | | | 125 | 200 | C | C | C | C | 70 | | | | | | | A | A | | | A | | A | | | | | |
| Methyl Ethyl Ketone (MEK) CH ₃ COC ₂ H ₅ | | C | C | C | C | C | 200 | 70 | C | C | C | C | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Methyl Formate HCOOCH ₃ | | | | | | | 100 | C | C | 70 | C | | | A | A | A | | A | A | C | | A | A | A | A | A | A | A | A | |
| Methyl Isobutyl Carbinol (CH ₃) ₂ CHCH ₂ CH(CH ₃)OH | | | | | | 200 | 70 | 70 | 70 | 70 | 70 | 70 | | | | | | | | | | | | | | | | | | |
| Methyl Isobutyl Ketone (CH ₃) ₂ CHCH ₂ COCH ₃ | | C | C | C | C | C | 200 | 70 | C | C | C | C | 275 | A | | | | A | | | | | | | | | | | | |
| Methyl Isopropyl Ketone CH ₃ COCH(CH ₃) ₂ | | | | | | C | 150 | C | C | C | C | C | | | | | | | | | | | | | | | | | | |
| Methyl Methacrylate C ₅ H ₈ O ₂ | | | | | | 73 | 125 | 150 | C | C | 70 | C | C | | | | | | | C | | | | | | | | | | |
| Methyl Sulfate (CH ₃) ₂ SO ₄ | | | | | | 73 | 280 | 70 | | | | | | | | | | | | | | | | | | | | | | |
| Methylene Bromide CH ₂ Br ₂ | | | | | | C | 175 | 250 | C | C | C | C | 70 | | | | | B | B | B | | | | | | | | | | |
| Methylene Chloride CH ₂ Cl ₂ | | | | | | C | C | 250 | C | C | C | C | 70 | C | | | | B | B | B | | | | | | | | | | |
| Methylene Chlorobromide CH ₂ ClBr | | | | | | C | | | C | C | C | C | C | | | | | | A | A | | | | | | | | | | |
| Methylene Iodine CH ₂ I ₂ | | | | | | C | | 200 | 250 | | | | | 250 | | | | | | | | | | | | | | | | |
| Methylsulfuric Acid CH ₃ HSO ₄ | | | | | | 140 | 125 | | | | | | | | | | | | | | | | | | | | | | | |
| Milk | | 70 | 170 | | 225 | 400 | 250 | 180 | 200 | 160 | 300 | 550 | | B | B | B | B | C | C | C | C | C | C | C | A | A | A | A | C | A |
| Mineral Oil | | 70 | 185 | 120 | 140 | 280 | 300 | C | 140 | B to 70 | 70 | 300 | 550 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A |
| Molasses | | | | | | 73 | 140 | 150 | 300 | 100 | 150 | 150 | 150 | 185 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A |
| Monochloroacetic Acid CH ₂ CICOOH | 50% | 73 | 73 | 140 | 150 | 200 | C | 70 | C | C | 70 | | A | C | C | C | C | C | C | C | C | C | C | C | C | B | B | C | | |
| Monochlorobenzene C ₆ H ₅ Cl | Tech. Pure | | 73 | | 170 | 200 | C | C | C | C | 70 | C | A | A | A | | | A | A | A | A | A | A | A | A | A | A | A | | |
| Monoethanolamine HOCH ₂ CH ₂ NH ₂ | | | | | | C | C | 100 | 70 | 70 | C | C | 185 | | A | | C | | B | B | B | | B | A | A | B | | | | |
| Morpholine C ₄ H ₉ ONH | | | | | | | | 75 | 200 | 70 | C | C | C | 275 | | B | B | | B | B | B | | B | B | B | B | B | B | B | |
| Motor Oil | | | | | | 185 | 73 | 140 | | 350 | C | 180 | | 250 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A |
| Muriatic Acid | 37% | C | 160 | 150 | 140 | 280 | 250 | 150 | C | 100 | | 100 | | C | C | C | C | C | C | C | C | C | C | B | C | B | C | C | C | |
| Naphtha | | B to 70 | 73 | 73 | 140 | 280 | 200 | C | 140 | C | C | 150 | 550 | | A | A | B | | A | A | A | A | A | A | A | A | A | A | A | |
| Naphthalene C ₁₀ H ₈ | | B to 70 | | | | C | 200 | 250 | C | C | C | C | 170 | 275 | | A | A | B | | A | A | A | A | A | A | A | A | A | A | |
| Natural Gas | | | | | | 73 | 140 | 280 | 300 | C | 140 | 140 | 140 | 185 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Nickel Acetate Ni(OOC ₂ H ₅) ₂ •4H ₂ O | | | | | | 73 | 250 | 300 | 70 | 70 | C | | C | | | | | | | | | | | | | | | | C | |
| Nickel Ammonium Sulfate NiSO ₄ •(NH ₄) ₂ SO ₄ •6H ₂ O | | | | | | 250 | | 140 | 200 | 160 | | | | | C | C | C | C | C | C | | | | | | | | | | C |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|---------|---------|----------|---------------|---------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|---------------------|-----------------|----------|---------|----------|-------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (65% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE SERIES S.S. | 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Nickel Chloride NiCl ₂ | Sat'd. | 185 | 180 | 140 | 280 | 406 | 210 | 180 | 200 | 160 | 210 | 275 | A | C | C | B | | C | C | C | | | | | A | A | A | C | A | | | |
| Nickel Nitrate Ni(NO ₃) ₂ •6H ₂ O | Sat'd. | | | 140 | 280 | 400 | 210 | 180 | | 250 | 275 | A | C | C | | | C | C | C | | A | A | A | A | C | | | C | | | | |
| Nickel Sulfate NiSO ₄ | Sat'd. | 185 | 180 | 140 | 280 | 400 | 210 | | 200 | 160 | 300 | | A | C | C | B | | C | C | C | | | | | | | | A | A | A | | |
| Nicotine C ₁₀ H ₁₄ N ₂ | | | | 140 | 70 | | C | 70 | C | | | | | | | | | | | | | | | | B | A | A | B | | | | |
| Nicotine Acid CsH ₄ NOOH | | | | 140 | 250 | | 70 | | 140 | | | | B | B | | | | C | C | C | | | | | B | B | B | B | B | A | | |
| Nitric Acid HNO ₃ | <10% | 73 | 185 | 140 | 140 | 175 | 250 | 70 | C | 100 | C | 185 | 550 | A | C | C | C | C | C | C | C | C | B | A | A | A | C | | C | C | | |
| Nitric Acid HNO ₃ | 30% | C | 150 | 73 | 140 | 125 | 250 | 70 | C | 100 | C | 160 | 275 | C | C | C | C | C | C | C | C | C | B | A | A | A | | | C | C | | |
| Nitric Acid HNO ₃ | 40% | C | 120 | C | 100 | 125 | 250 | C | C | 70 | C | 140 | C | C | C | C | C | C | C | C | C | C | B | A | A | A | | | C | C | | |
| Nitric Acid HNO ₃ | 50% | C | 120 | C | 100 | 125 | 250 | C | C | 70 | C | 120 | C | C | C | C | C | C | C | C | C | C | B | A | A | A | | | C | C | | |
| Nitric Acid HNO ₃ | 70% | C | 100 | C | 73 | 125 | 250 | C | C | C | C | 100 | C | C | C | C | C | C | C | C | C | C | C | A | A | A | | | B | C | | |
| Nitric Acid HNO ₃ •NOx | Fuming | C | C | C | C | C | 70 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | A | A | C | | | B | C | |
| Nitrobenzene C ₆ H ₅ NO ₂ | | | | 73 | C | 73 | 400 | C | | C | C | 70 | C | A | B | B | | A | A | A | | | | | A | A | A | A | A | A | | |
| Nitroethane CH ₃ CH ₂ NO ₂ | Tech. Pure | | | | | 70 | | C | | C | C | | | | | | | | | | | | | | | | | | | | | |
| Nitrogen Gas N ₂ | | | | | 275 | 300 | | 140 | 100 | 140 | 185 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Nitroglycerin CH ₃ NO ₃ CHNO ₃ CH ₂ NO ₃ | | | | | C | 125 | 70 | | | | | | B | B | | | | B | B | | | | | | A | A | B | | | | | |
| Nitroglycol C ₂ H ₄ N ₂ O ₆ | | | | | C | | | | 70 | 70 | | | | | | | | | | | | | | | | | | | | | | |
| Nitromethane CH ₃ NO ₂ | Tech. Pure | | | | | 120 | | 70 | C | | C | | 275 | | | | | | | | | | | | | | | | | | | |
| Nitrous Acid HNO | 10% | | | | 73 | 230 | 400 | | C | | | 100 | 275 | | C | C | C | C | C | C | C | C | | B | B | B | C | | C | C | | |
| Nitrous Oxide N ₂ O | | | | | 73 | 73 | C | 400 | | C | B to 140 | C | 70 | 550 | A | B | B | | C | B | B | | | | A | A | C | A | | | | |
| n-Octane CH ₃ H ₁₈ | | | | | | 275 | 400 | C | B to 70 | | | 70 | | 550 | A | A | A | A | A | A | A | A | | A | A | A | A | A | A | A | A | |
| Oleic Acid CH ₃ (CH ₂) ₇ CH(CH ₂) ₇ COOH | | | | | 185 | 150 | 140 | 250 | 250 | B to 70 | 100 | 70 | B to 70 | 185 | 550 | A | B | B | A | B | B | C | | B | A | A | A | A | A | A | A | |
| Oleum | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Olive Oil | | | | | | | 250 | 350 | | 140 | B to 100 | 140 | 150 | | | A | A | A | A | A | A | A | A | | A | A | A | A | A | A | A | A |
| Oxalic Acid HOOCOOH | 50% | | | | 185 | 180 | 140 | 125 | 300 | 150 | C | | 100 | 100 | 275 | A | C | C | C | C | C | C | B | A | A | A | A | A | A | A | C | |
| Oxygen (Gas) O ₂ | | | | | 185 | 150 | 140 | 280 | 406 | 210 | B to 70 | 140 | 140 | 185 | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Ozone O ₃ | | | | | | 140 | 225 | 300 | 210 | C | 140 | C | 185 | 275 | C | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|---------|--------------------------------|------|--------|---------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|-------------------------|----------|---------|----------|-------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Palm Oil | | | | | 200 | 200 | C | 140 | C | | 70 | | | | | | | | | | | | | | | | | | | | |
| Palmitic Acid CH ₃ (CH ₂) ₁₄ COOH | 10% | 73 | 180 | 140 | 250 | 300 | 70 | 100 | 70 | C | 185 | 550 | | | B | B | B | A | B | B | B | B | B | A | A | A | A | A | A | A | |
| Palmitic Acid CH ₃ (CH ₂) ₁₄ COOH | 70% | 73 | 180 | 73 | 250 | 300 | | 100 | C | C | 185 | 550 | | | B | B | B | A | B | B | B | B | B | A | A | A | A | A | A | A | |
| Parafin C ₃₆ H ₇₄ | B to 70 | | | 140 | 250 | 250 | C | 100 | | 140 | 300 | 550 | | | A | A | A | | B | A | A | B | B | A | A | A | A | A | A | A | |
| Peanut Oil | | C | | C | 250 | 250 | C | 100 | | | 150 | | | | A | A | | | A | A | | | A | A | | | | | | | |
| Pentachlorophenol C ₆ Cl ₅ OH | C | C | | C | | 70 | C | C | C | C | 250 | | | | | | | | | | | | | | | | | | | | |
| n-Pentane CH ₃ (CH ₂) ₃ CH ₃ | C | | | | | 100 | C | 100 | | 70 | 100 | 550 | | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Peracetic Acid CH ₃ COOOH | 40% | | | | 73 | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Perchloric Acid HClO ₄ | 10% | 140 | 73 | 73 | 200 | 250 | 70 | C | 70 | 70 | 70 | 275 | A | | | | | C | | | | | | A | A | A | | | | | |
| Perchloric Acid HClO ₄ | 70% | 185 | 73 | | 125 | | 70 | C | C | C | 185 | C | C | | | | | C | | | | | | B | B | A | | | | | |
| Perchloroethylene Cl ₂ C:CCl ₂ | | | | | 275 | 200 | C | C | C | C | 200 | | | | B | B | | | B | B | B | | B | A | A | A | A | A | A | | |
| Perphosphate | | | 170 | 170 | 140 | | 250 | 70 | 70 | | 70 | | | | | | | | | | | | | | | | | | | | |
| Phenol C ₆ H ₅ OH | C | 73 | 73 | 73 | 125 | | 70 | C | C | C | 200 | C | A | A | A | C | | C | C | C | | C | A | A | A | A | A | A | A | | |
| Phenylhydrazine C ₆ H ₅ NHNH ₂ | | | | C | 125 | B to 70 | C | C | C | | C | | | | | | | | | | | | | | | | | | | | |
| Phosphate Esters | | | | | | | C | | C | 100 | | | | C | C | | | C | C | | | C | A | A | A | A | A | | | | |
| Phosphoric Acid H ₃ PO ₄ | 10% | 210 | 180 | 140 | 275 | 300 | 140 | 70 | 200 | 140 | 200 | 550 | A | C | C | C | C | C | C | C | C | C | B | A | A | A | C | C | | | |
| Phosphoric Acid H ₃ PO ₄ | 50% | 210 | 180 | 140 | 275 | 300 | 70 | C | 200 | 70 | 200 | 550 | A | C | C | C | C | C | C | C | C | C | C | B | A | A | A | C | C | | |
| Phosphoric Acid H ₃ PO ₄ | 85% | 73 | 180 | 140 | 275 | 300 | 70 | C | 200 | C | 200 | 275 | A | C | C | C | C | C | C | C | C | C | C | B | A | B | A | C | C | | |
| Phosphoric Anhydride P ₂ O ₅ | | 73 | 73 | 73 | 200 | | | | | | | | | | | | | | | | | C | | A | A | | B | | | | |
| Phosphorus (Red) | | | | | 70 | 75 | 300 | | | | | | | | | | | | | | | | | A | A | | | | | | |
| Phosphorus (Yellow) | | | | | 73 | | 300 | | | | | | | | | | | | | | | | | | | | | | | | |
| Phosphorus Pentoxide P ₂ O ₅ | | 73 | 73 | 73 | 200 | | 140 | | | | | | | | | C | | | B | | | | A | A | | | C | | | | |
| Phosphorus Trichloride PCl ₃ | | | | C | 200 | 300 | | C | C | C | | | | A | | | | | | | | | A | A | A | | C | | | | |
| Photographic Solutions | | 185 | 150 | 140 | | | | | 100 | 100 | 185 | | | | | | | C | | B | | | A | A | | | | | | | |
| Phthalic Acid C ₆ H ₄ (COOH) ₂ | | | | 73 | 200 | | | C | 140 | C | 140 | 550 | A | A | A | | | B | B | C | | B | A | A | A | B | A | A | | | |
| Picric Acid C ₆ H ₂ (NO ₂) ₃ OH | 10% | C | 140 | 170 | 170 | 73 | | 140 | C | 70 | 70 | 140 | | C | C | C | C | C | C | C | C | C | B | A | | A | C | A | C | | |
| Pine Oil | | | | | | | | 70 | | C | 70 | | | C | C | B | | B | B | B | | B | A | A | A | A | A | A | | | |
| Plating Solutions (Brass) | | | 185 | 180 | 140 | 200 | 300 | 70 | | | 100 | 70 | | | | | | | | | | | | | | | | | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|--------|---------|----------|---------------|-------------------------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|----------------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROL | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Plating Solutions (Cadmium) | | 185 | 180 | 140 | 200 | 300 | 70 | | | 100 | 70 | | | | | | | | | | | | | | | | | | | | |
| Plating Solutions (Chrome) | | 210 | 180 | 140 | 200 | 300 | | | | 160 | | | | | | | | | | | | | | A | A | | | | | | |
| Plating Solutions (Copper) | | 210 | 180 | 140 | 200 | 300 | 70 | | | 160 | 70 | | | | | | | | | | | | | | | | | | | | |
| Plating Solutions (Gold) | | 185 | 180 | 140 | | 300 | 70 | | | 125 | 70 | | | | | | | | | | | | | | | | | | | | |
| Plating Solutions (Lead) | | 210 | 180 | 140 | 200 | 300 | 70 | 70 | | 70 | 70 | | | | | | | | | | | | | | | | | | | | |
| Plating Solutions (Nickel) | | 210 | 180 | 140 | 200 | 300 | 70 | | | 70 | | | A | C | C | | | | | | | | A | A* | | | | C | | | |
| Plating Solutions (Rhodium) | | 185 | 180 | 140 | 200 | 300 | | | | 70 | | | | | | | | | | | | | | | | | | | | | |
| Plating Solutions (Silver) | | 185 | 180 | 140 | 200 | 300 | 70 | | | 70 | 70 | | | | | | | | | | | | | A | A | | | A | | | |
| Plating Solutions (Tin) | | 210 | 180 | 140 | 200 | 300 | 100 | | | 140 | | | | | | | | | | | | | | | A | A | | | | | |
| Plating Solutions (Zinc) | | 185 | 180 | 140 | 200 | 300 | 70 | | | 70 | | | | | | | | | | | | | | B | | | | | | | |
| Polysulfide Liquor | | | | | | 300 | 70 | 70 | 70 | 70 | 100 | | C | C | C | C | B | B | | B | B | B | B | B | B | B | C | | | | |
| Polyvinyl Acetate (C ₄ H ₆ O ₂) | | | | | 275 | 350 | 70 | 70 | 70 | 70 | 70 | | B | B | B | A | A | C | | A | B | B | B | B | B | | | | | | |
| Potash | | | | | | | | | | | | | See Potassium Carbonate | | | | | | | | | | | | | | | | | | |
| Potassium Alum ALK(SO ₄) ₂ •12H ₂ O | | | | | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 200 | | | | | | | | | | | | | | | | | | | |
| Potassium Aluminum Sulphate AIK (H ₂ SO ₄) ₂ | | | | | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 200 | | | | B | C | | C | | B | A | | A | A | | | B | B | | |
| Potassium Amyl Xanthate C ₆ H ₁₁ OS ₂ K | | | | | 73 | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Potassium Bicarbonate KH ₂ CO ₃ | Sat'd. | 73 | 170 | 140 | 200 | 400 | 170 | 70 | 200 | 160 | 200 | 275 | | | | | | | A | | A | A | | | | | A | | | | |
| Potassium Bichromate K ₂ Cr ₂ O ₇ | Sat'd. | | | | 140 | 230 | 400 | 170 | 180 | | 300 | B | A | | A | | B | | B | | B | A | | A | | | A | | | | |
| Potassium Bisulfate KHSO ₄ | | | | | 140 | 275 | 400 | 170 | 180 | 140 | 140 | 200 | | A | B | B | B | | C | C | C | C | | A | A | C | | | | | |
| Potassium Bromate KBrO ₃ | | | | | 180 | 140 | 275 | 400 | 180 | 140 | 140 | 250 | | | | | | C | A | A | | A | A | A | A | | | | | | |
| Potassium Bromide KBr | | | | | 180 | 140 | 280 | 400 | 170 | 180 | 200 | 160 | 200 | 275 | A | B | B | B | C | C | C | | A | A | A | | | | | | |
| Potassium Carbonate K ₂ CO ₃ | | 70 | | 180 | 140 | 280 | 400 | 170 | 180 | 200 | 160 | 200 | 550 | A | B | B | B | A | A | A | A | A | A | A | A | A | A | A | B | | |
| Potassium Chlorate KClO ₃ (Aqueous) | | | | | 180 | 140 | 200 | 400 | 140 | B to 70 | 140 | 100 | 140 | | C | B | B | | A | A | A | A | A | A | A | A | A | A | A | B | |
| Potassium Chloride KCl | | | | | 185 | 180 | 140 | 280 | 400 | 210 | 180 | 200 | 160 | 200 | | | B | A | A | B | B | B | C | B | B | B | A | A | A | A | A |
| Potassium Chromate K ₂ CrO ₄ | | | | | 140 | 280 | 400 | 170 | 140 | 70 | 70 | 200 | | C | A | A | B | | B | B | B | B | | A | A | A | A | A | | | |
| Potassium Cyanide KCN | | | | | 185 | | 140 | 280 | 400 | 140 | 180 | 200 | 160 | 185 | | C | C | C | C | B | B | B | B | | A | A | A | A | A | A | C |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|---------|---------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------|----------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPMI | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE SS. | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Potassium Dichromate K ₂ Cr ₂ O ₇ | Sat'd. | 185 | | 140 | 280 | 400 | 170 | 180 | 200 | | 300 | 275 | C | B | B | C | | B | B | C | | A | A | A | A | | | | | |
| Potassium Ethyl Xanthate KS ₂ COC ₂ H ₅ | | | | 73 | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Potassium Ferricyanide K ₃ Fe(CN) ₆ | | | | 140 | 280 | 400 | 140 | 70 | 200 | 150 | 140 | 550 | | C | C | | | B | B | C | | | | A | A | A | A | C | | |
| Potassium Ferrocyanide K ₄ Fe(CN) ₆ •3H ₂ O | | | | 140 | 280 | 400 | 140 | 70 | 200 | 150 | 140 | 550 | | B | B | C | C | C | C | C | | B | A | A | A | | C | C | | |
| Potassium Fluoride KF | | | | 140 | 275 | 400 | 140 | 180 | | | 250 | A | | | | | | | | | | | | A | A | A | A | | | |
| Potassium Hydroxide KOH | 25% | 140 | B | 180 | 140 | C | 300 | 140 | B | 140 | 160 | C | 275 | A | C | C | C | B | B | B | B | | A | A | A | A | A | C | | |
| Potassium Hypochlorite KClO | | C | 180 | C | 140 | 200 | 400 | C | C to 70 | 70 | | 70 | | C | C | | | | | | | C | | | A | A | C | | | |
| Potassium Iodide KI | | | 73 | | 250 | 400 | 140 | 100 | 140 | 160 | 180 | | A | B | B | | | | | | B | B | | A | A | A | | | | |
| Potassium Nitrate KNO ₃ | | | | 140 | 280 | 400 | 210 | 180 | 140 | 140 | 250 | 275 | C | A | A | B | B | B | B | B | | A | A | A | A | A | A | A | | |
| Potassium Perborate | | 170 | 170 | 140 | 275 | 400 | | 70 | | 70 | | | A | | | | | | | | | | | | | | | | | |
| Potassium Perchlorate KClO ₄ | | | | 140 | 200 | 200 | 140 | C | 150 | | 150 | | | | | | | | | | | | | | | | | | | |
| Potassium Permanganate KMnO ₄ | 10% | 180 | 150 | 140 | 250 | 400 | 210 | C | 100 | 100 | 140 | | | B | B | | | A | A | A | | | A | A | A | A | A | A | | |
| Potassium Permanganate KMnO ₄ | 25% | 150 | 150 | 73 | 250 | 400 | 140 | C | 100 | 100 | 140 | | | B | B | | | A | A | A | | | A | A | A | A | A | A | | |
| Potassium Persulfate K ₂ S ₂ O ₈ | | | | 140 | 125 | 400 | 210 | C | 200 | 140 | 200 | | | | | | | | | | | | | | | | | | | |
| Potassium Sulfate K ₂ SO ₄ | | | | 180 | 140 | 280 | 200 | 210 | 140 | 140 | 140 | 250 | | A | A | A | B | B | B | A | A | A | B | A | A | A | A | A | A | |
| Potassium Sulfide K ₂ S | | | | | | 275 | 300 | | 100 | | 70 | 100 | 550 | | C | C | C | C | C | C | B | | B | B | B | C | A | C | | |
| Potassium Sulfite K ₂ SO ₃ •2H ₂ O | | | | | | 300 | 140 | 70 | | 70 | 200 | | | B | B | B | | C | C | C | | | A | A | B | | | | | |
| Potassium Tetraborate K ₂ B ₄ O ₇ •8H ₂ O | | | | | 140 | 275 | 400 | 170 | 180 | 140 | 140 | 200 | | A | | | | | | | A | A | A | A | | | | | | |
| Potassium Tripolyphosphate K ₅ P ₃ O ₁₀ | | | | | | 300 | | 70 | | 70 | 100 | | A | | | B | | A | A | A | | | A | A | A | A | C | | | |
| Propane C ₃ H ₈ | | 73 | | 140 | 280 | 300 | C | 70 | B to 70 | 70 | 70 | 550 | A | A | A | A | A | A | A | A | A | | A | A | A | A | A | A | | |
| Propargyl Alcohol HC:CHCH ₂ OH | | C | | 140 | 100 | 140 | | 140 | | 140 | C | 140 | | | | | | | | | | | | | | | | | | |
| Propionic Acid CH ₃ CH ₂ CO ₂ H | | C | | | | | | | 140 | 70 | C | | | | | | | | | | | | | | | | | | A | |
| Propyl Acetate C ₃ H ₇ OOCCH ₃ | | | | | | 100 | 140 | B to 70 | C | C | C | C | 550 | | | | A | | A | | | A | A | A | A | A | A | A | | |
| Propyl Alcohol CH ₃ CH ₂ CH ₂ OH | | C | | 140 | | 140 | 350 | 140 | 140 | 140 | 140 | 550 | | A | A | A | A | A | A | A | | A | A | A | A | A | A | A | | |
| n-Propyl Bromide CH ₃ CH ₂ CH ₂ Br | | | | | | 300 | B to 70 | | | 70 | 70 | | | B | B | B | | B | B | B | | | A | | A | B | | | | |
| Propylene Dichloride CH ₃ CClCHCl | | | | | C | 200 | | C | C | C | C | B to 70 | | | | | | | | A | | | | | A | | | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|---------|--------|----------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|---------------------------------------|----------|---------|----------|---------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROXYL | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NIPLATED DUCTILE IRON SERIES 400 S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Propylene Glycol CH ₃ CHOHCH ₂ OH | <25% | C | 180 | 140 | 140 | 150 | 300 | 70 | 180 | 70 | 100 | 140 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | C | A | |
| Propylene Glycol CH ₃ CHOHCH ₂ OH | >25% | C | C | 140 | C | 150 | 300 | 70 | 180 | 70 | 100 | 140 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | C | A | |
| Propylene Oxide CH ₃ CHCH ₂ O | | | | C | C | 150 | 70 | C | C | C | C | | | | | | | | | | | | A | | | A | | | | |
| n-Propyl Nitrate C ₃ H ₇ NO ₃ | | | | | | 200 | 70 | C | C | C | C | | | | | | | | | | | | A | A | | A | | A | | |
| Pyridine N(CH ₃) ₂ CH | | | | 73 | C | C | | B to 70 | C | C | C | C | | | B | B | | | B | B | B | | B | C | B | | A | B | | |
| Pyrogallic Acid C ₆ H ₃ (OH) ₃ | | | | | 73 | 150 | 150 | | 70 | | 70 | | | | A | A | | | A | A | A | | A | A | A | A | A | A | A | A |
| Pyrrole CHNH(CH ₂) ₂ CH | | | | | | | | C | C | C | C | C | | | B | B | | | B | B | B | | B | | B | | B | B | | |
| Quinone C ₆ H ₄ O ₂ | | | | | | | 100 | | C | | C | | | | | | | | A | A | | | A | A | A | | A | | A | |
| Rosin | | | | | | 200 | | 70 | 70 | 70 | 100 | | | | C | C | | | C | C | C | | C | A | A | A | A | A | A | A |
| Salicylaldehyde C ₆ H ₅ OHCHO | | | | | C | 125 | 200 | 70 | 70 | | | 70 | | | | | | | | | | | | | | | | | | |
| Salicylic Acid C ₆ H ₅ (OH)(COOH) | | | | | | 140 | 200 | 300 | 210 | C | 70 | C | 185 | | | B | B | | | C | C | C | | C | A | | A | B | | |
| Selenic Acid H ₂ SeO ₄ | | | | | | 140 | 150 | | | 70 | 70 | 70 | | | | | | | | | | | | | | | | | | |
| Silicic Acid SiO ₂ •nH ₂ O | | | | | 140 | | 400 | 140 | 100 | 140 | 140 | 200 | | | | | | | | | | | | | | | | | | |
| Silicone Oil | | | | 150 | 150 | 73 | 250 | 350 | 140 | 140 | 140 | 70 | 185 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Silver Chloride AgCl | | | | | | | | | | | | | | | A | C | C | C | C | C | C | C | C | C | C | C | A to 70 | A | C | |
| Silver Cyanide AgCN | | | | 185 | | 140 | 280 | 350 | 140 | C | | 70 | 140 | | | C | C | C | C | C | C | C | C | A to 100 | A to 70 | A | | C | | |
| Silver Nitrate AgNO ₃ | | 70 | 185 | 180 | 140 | 280 | 350 | 210 | 140 | 200 | 160 | 250 | 550 | A | C | C | C | C | C | C | C | C | B | A | | A | C | | C | |
| Silver Sulfate Ag ₂ SO ₄ | | 70 | | | 140 | 250 | 350 | 170 | 140 | | | 200 | | A | | | | | | | | | | | | | | | | |
| Soaps | | 70 | 185 | 73 | 140 | | 400 | 210 | 180 | 140 | 140 | 250 | 550 | | B | B | A | | B | B | B | | B | A | A | A | A | B | A | |
| Sodium Acetate NaC ₂ H ₃ O ₂ | Sat'd. | | 185 | 180 | 140 | 280 | 400 | 170 | C | 70 | | C | 275 | | A | A | B | | B | B | C | | B | B | A | | A | A | A | |
| Sodium Alum AlNa(SO ₄) ₂ •12H ₂ O | | | | | 140 | 280 | | 170 | 180 | 140 | 140 | 210 | | | | | | | | | | C | | | | | | | C | |
| Sodium Aluminate NaAlO ₂ | Sat'd. | | | | | | 300 | 200 | 180 | 140 | 140 | 200 | 275 | | C | C | B | | B | B | A | | B | | A | | A | A | A | |
| Sodium Benzoate C ₆ H ₅ COONa | | | | 140 | 170 | 140 | 280 | 300 | 210 | 140 | | | 200 | 550 | | | | | | | | | | | | | | | A | |
| Sodium Bicarbonate NaHCO ₃ | | 70 | 185 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | 300 | 550 | | A | A | B | B | A | A | C | | A | A | A | A | A | A | A | |
| Sodium Bichromate Na ₂ Cr ₂ O ₇ •2H ₂ O | Sat'd. | | 140 | 140 | 140 | 250 | 400 | 140 | 140 | 70 | 70 | 200 | 275 | C | C | C | | | | | | | | A | A | A | A | A | | |
| Sodium Bisulfite NaHSO ₃ | | 70 | | 180 | 140 | 280 | | 200 | 180 | 100 | 140 | 250 | | | C | C | C | C | C | C | C | | C | B | A | | A | A | | C |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | | METALS | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|----------|-----|----------|--------------------------------|---------|--------|----------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-------------------------------------|------------------|----------|---------|----------|-------|----------|-------------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE IRON SERIES SS-3. | 400 SERIES SS-3. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C |
| Sodium Bisulfite NaHSO ₃ | | 185 | 180 | 140 | 280 | 400 | 200 | 180 | 200 | 140 | 250 | 550 | | B | B | | | C | C | C | | C | | A | A | C | A | | | |
| Sodium Borate (Borax) Na ₂ B ₄ O ₇ •10H ₂ O | Sat'd. | | 73 | | | 300 | 140 | 70 | 100 | 100 | 140 | 550 | A | A | A | | B | B | | | B | A | A | A | A | | | | | |
| Sodium Bromide NaBr | Sat'd. | 180 | 180 | 140 | 280 | 300 | 210 | 70 | | 70 | 250 | 275 | A | B | B | | C | C | C | | C | | A | A | A | A | | | | |
| Sodium Carbonate Na ₂ CO ₃ | 70 | 185 | 180 | 140 | 280 | 400 | 140 | 140 | 140 | 140 | 300 | 550 | | A | A | B | B | A | A | A | A | | A | A | A | B | A | C | | |
| Sodium Chlorate NaClO ₃ | Sat'd. | | 180 | 73 | 250 | 350 | B to 140 | B to 70 | | B to 140 | 100 | | | A | A | C | | B | B | B | | B | B | A | A | A | C | | | |
| Sodium Chloride NaCl | . | 210 | 180 | 140 | 280 | 350 | 140 | 140 | 100 | 160 | 200 | | | B | A | A | A | B | B | B | B | C | A | B | B | B | A | A | A | |
| Sodium Chlorite NaClO ₂ | 25% | 73 | | C | 250 | 200 | C | C | 140 | | C | | C | | | | | | | | | | | | | | | | | |
| Sodium Chromate Na ₂ CrO ₄ •10H ₂ O | | | | | 200 | | 70 | 70 | | 70 | 70 | | C | A | A | | B | B | B | | B | A | A | A | A | A | | | | |
| Sodium Cyanide NaCN | | 185 | 180 | 140 | 280 | 350 | 140 | 140 | 140 | 140 | 200 | 275 | C | C | C | | C | A | A | A | | | A | A | A | A | A | C | | |
| Sodium Dichromate Na ₂ Cr ₂ O ₇ •2H ₂ O | 20% | 185 | 180 | 140 | 200 | 300 | 140 | C | 200 | C | 200 | | C | C | C | C | B | B | B | | | | A | A | B | | | | | |
| Sodium Ferricyanide Na ₃ [Fe(CN) ₆]•H ₂ O | Sat'd. | 140 | 140 | 100 | 275 | 350 | 140 | 70 | | | 140 | | C | C | | | C | C | | | | | A | A | | | | | | |
| Sodium Ferrocyanide Na ₄ [Fe(CN) ₆]•10H ₂ O | Sat'd. | 185 | | 140 | 275 | 350 | 140 | 70 | | | 140 | | | | | | | | | | | | A | A | A | | | | | |
| Sodium Fluoride NaF | | | 140 | 185 | 140 | 280 | 350 | 140 | 70 | 140 | 70 | 140 | 275 | A | A | A | B | C | C | C | | | A | A | A | | | | | |
| Sodium Hydroxide NaOH | <10% | 140 | B | 180 | 140 | C | 400 | 180 | 140 | 200 | 160 | C | 275 | A | A | A | | A | A | | | B | A | A | A | A | A | C | | |
| Sodium Hydroxide NaOH (Caustic Soda) | 30% | 70 | B | 180 | 140 | C | 350 | 140 | 100 | 140 | 160 | C | 275 | A | A | | B | | B | B | | B | A | A | A | A | A | C | | |
| Sodium Hydroxide NaOH | 50% | 70 | B | 180 | 140 | C | 350 | 140 | C | 140 | 160 | C | 275 | A | B | C | C | C | B | B | B | B | A | A | A | A | A | C | B | |
| Sodium Hydroxide NaOH | 70% | C | B | 180 | 140 | C | 350 | 70 | C | 100 | 100 | C | | A | C | C | C | C | B | B | B | B | B | A | A | A | A | A | C | B |
| Sodium Hypochlorite NaOCl•5H ₂ O | 5% | C | 185 | B to 100 | 140 | B to 200 | 350 | 70 | C | 150 | C | 185 | C | | C | C | C | C | C | C | C | C | C | C | C | C | C | A | C | C |
| Sodium Hypochlorite NaOCl•5H ₂ O | Sat'd. | C | 185 | C | 140 | B to 200 | 350 | C | C | 150 | C | 140 | C | | C | C | C | C | C | C | C | C | C | C | C | C | C | A | C | C |
| Sodium Iodide NaI | | | | | | 275 | | | | 140 | 160 | | | A | | | | | | | | | | | | | | | | |
| Sodium Metaphosphate (NaPO ₃) _n | | | | 73 | | 280 | | 70 | 70 | 70 | | 70 | | A | C | C | C | | C | C | C | | | A | A | B | | | | |
| Sodium Nitrate NaNO ₃ | Sat'd. | 185 | 180 | 140 | 280 | 400 | 210 | 140 | 140 | 140 | 225 | 275 | A | A | A | B | B | B | A | A | A | A | A | A | A | A | B | A | B | |
| Sodium Nitrite NaNO ₂ | | | | | 140 | 280 | 400 | 170 | C | 140 | 140 | 200 | | A | A | | | B | B | B | | | A | A | A | A | | | | |
| Sodium Palmitate CH ₃ (CH ₂) ₁₄ COONa | 5% | | | | | 250 | 350 | | | | | | | | | | | | | | | | | | | | | | | |
| Sodium Perborate NaBO ₂ •H ₂ O ₂ •3H ₂ O | | | | 73 | 140 | | 350 | 70 | 70 | 70 | 70 | 275 | A | C | C | | | B | B | B | | | A | A | A | A | A | A | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | METALS | | | | | | | | | | | | | | | | | | |
|--|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|---------|---------|----------|---------------|--------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|----------|-----------------------|----------------|----------|---------|----------|-------|----------|-------------|----------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NIMON | NI PLATED DUCTILE SS. | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM |
| Sodium Perchlorate NaClO ₄ | | 170 | 170 | | 140 | 250 | 350 | | B to 70 | | | | | | | | | | | | | | | | | | | | | | |
| Sodium Peroxide Na ₂ O ₂ | | | | 140 | 200 | 250 | 140 | | B to 70 | 200 | 70 | 185 | | C | C | C | C | C | C | C | C | C | A | A | A | A | A | B | | B | |
| Sodium Phosphate NaH ₂ PO ₄ | Acid | | | 180 | | 280 | 400 | 170 | 140 | 200 | 140 | 200 | 550 | A | B | B | B | B | B | B | B | A | B | A | A | A | A | B | A | B | |
| Sodium Phosphate NaH ₂ PO ₄ | Alkaline | | | 180 | | 280 | 400 | 170 | 140 | 200 | 140 | 200 | 550 | A | B | B | B | B | B | B | B | A | B | A | A | A | A | B | A | B | |
| Sodium Phosphate NaH ₂ PO ₄ | Neutral | | | 180 | | 280 | 400 | 170 | 140 | 200 | 140 | 200 | 550 | A | B | B | B | B | B | B | B | A | B | A | A | A | A | B | A | B | |
| Sodium Silicate Na ₂ SiO ₃ | | | | 180 | | 280 | | 200 | 140 | 200 | 140 | 200 | 550 | | C | C | B | | A | A | A | | A | A | A | A | A | A | A | A | A |
| Sodium Sulfate Na ₂ SO ₄ | Sat'd. | 70 | 185 | 150 | 140 | 280 | 400 | 140 | 140 | 140 | 140 | 200 | 275 | A | A | A | B | B | A | A | A | A | A | A | A | A | A | A | A | A | |
| Sodium Sulfide Na ₂ S | | 70 | 185 | 150 | 140 | 280 | 350 | 140 | 180 | 200 | 140 | 200 | 550 | | C | C | C | C | B | B | C | B | B | A | A | A | A | A | A | A | C |
| Sodium Sulfite Na ₂ SO ₃ | | 70 | 185 | 180 | 140 | 280 | 350 | 140 | 140 | 140 | 140 | 200 | | | A | A | C | | B | B | B | | B | B | A | A | A | C | A | A | |
| Sodium Thiosulphate NaS ₂ O ₃ •5H ₂ O | | | | 150 | 140 | 280 | 350 | 200 | 140 | 200 | 160 | 200 | 550 | | B | B | C | | C | C | C | | C | A | A | A | A | A | A | A | |
| Sour Crude Oil | | | | | 140 | 280 | | C | C | 70 | C | 200 | | | C | | | | A | A | A | | B | A | A | A | A | A | A | | |
| Soybean Oil | | | | | | 250 | 400 | C | 140 | 200 | 70 | 250 | | | A | A | B | | A | A | B | A | A | A | A | A | A | A | A | | |
| Stannic Chloride SnCl ₄ | | | 185 | | 140 | 280 | 350 | 100 | 140 | 70 | C | 200 | 275 | A | C | C | C | C | C | C | C | C | C | C | C | C | A | C | C | C | |
| Stannous Chloride SnCl ₂ | 15% | 185 | | 140 | 280 | 350 | 70 | 140 | 200 | 160 | 200 | | | A | C | C | C | C | C | C | C | C | C | C | C | C | A | C | | | |
| Starch | | | | | 140 | 200 | 300 | 170 | 180 | 200 | 160 | 200 | | | B | B | B | B | B | B | B | B | B | A | A | A | A | A | A | A | |
| Steam (Low Pressure) | | | | | | 280 | 400 | C | C | C | C | C | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | |
| Steam (Medium Pressure) | | | | | | | 400 | C | C | C | C | C | | | A | A | A | A | A | A | A | A | A | A | A | A | A | B | A | B | A |
| Steam (High Pressure) | | | | | | | C | C | C | C | C | C | | | C | C | C | C | C | B | A | C | B | A | A | A | C | A | C | C | |
| Stearic Acid CH(CH ₂) ₁₆ COOH | | 185 | 73 | 140 | 275 | 350 | C | 140 | 70 | 70 | 100 | 550 | A | A | A | C | B | C | C | C | B | C | A | A | A | A | A | A | A | A | |
| Stoddard's Solvent | | | | | | 280 | | C | 140 | C | C | 185 | | | A | A | | | A | A | A | | A | A | A | A | A | A | A | A | A |
| Styrene (C ₆ H ₅ CHCH ₂) _n | | | | | | 180 | 350 | C | C | C | C | 100 | 275 | | B | B | B | | B | B | B | | B | A | A | A | A | A | A | A | |
| Succinic Acid CO ₂ H(CH ₂) ₂ CO ₂ H | | | | | 150 | 140 | 150 | 200 | 70 | 70 | | 70 | | | A | A | | | A | A | A | | A | A | A | A | A | A | A | A | |
| Sugar C ₆ H ₁₂ O ₆ | | | | | | 275 | 350 | 140 | 100 | 140 | 140 | 200 | | | C | C | | | B | C | | B | A | A | A | A | A | A | A | | |
| Sulfamic Acid HSO ₃ NH ₂ | 20% | | | 180 | 140 | C | | C | C | 70 | 70 | C | | | B | B | B | | C | C | C | | C | A | A | B | | | A | | |
| Sulfate Liquors (Oil) | | | | | 73 | | 200 | 70 | 70 | | 70 | | | | C | C | C | C | B | A | | | A | A | A | A | A | A | C | | |
| Sulfite Liquors | 6% | | | | | 140 | | 350 | 140 | 70 | 70 | 140 | | | | | | | | | | C | B | | A | A | A | | | | |
| Sulfur | S | | | | C | 140 | 250 | 350 | C | 70 | 70 | 250 | 275 | A | C | C | C | C | B | B | C | B | B | B | A | A | A | A | C | C | |
| Sulfur Chloride S ₂ Cl ₂ | | | C | | 73 | 350 | C | C | 70 | C | 70 | | | A | C | C | C | C | C | C | C | C | C | C | C | B | C | C | C | C | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | | | |
|---|---------------|------------------------------------|------|-----|-----|------|-----------------------------------|------|--------|---------|----------|---------------|----------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------|-------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|--|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED | DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER | |
| Sulfur Dioxide SO ₂ | Dry | C | 73 | 140 | 175 | 350 | 70 | C | 200 | C | 100 | 550 | A | A | A | B | A | A | A | A | A | A | A | A | A | A | A | A | A | | | | |
| Sulfur Dioxide SO ₂ | Wet | C | 73 | 73 | 150 | | 140 | C | 200 | | 140 | | A | C | B | B | C | | | | | C | A | C | A | A | A | B | C | | | | |
| Sulfur Trioxide SO ₃ | | | | | 140 | C | | 70 | C | C | C | 140 | | C | C | | C | | | | C | B | B | A | A | A | A | C | | | | | |
| Sulfuric Acid H ₂ SO ₄ | Up to 30% | 100 | 210 | 180 | 140 | 250 | 250 | 140 | C | 100 | 100 | 250 | | A | C | C | C | C | C | C | C | C | A | B | A | A | C | A | C | | | | |
| Sulfuric Acid H ₂ SO ₄ | 50% | 70 | 210 | 150 | 140 | 250 | 250 | 70 | 140 | 150 | C | 250 | C | A | C | C | C | C | C | C | C | C | A | C | A | A | C | A | C | | | | |
| Sulfuric Acid H ₂ SO ₄ | 60% | C | 210 | 150 | 140 | 250 | 250 | C | C | 150 | C | 250 | C | A | C | C | C | C | C | C | C | C | C | B | B | A | B | C | A | C | | | |
| Sulfuric Acid H ₂ SO ₄ | 70% | C | 210 | 120 | 140 | 200 | 200 | C | C | 150 | C | 200 | C | 212 | C | C | C | C | C | C | C | C | C | B | C | A | C | C | A | C | | | |
| Sulfuric Acid H ₂ SO ₄ | 80% | C | 180 | 73 | 140 | 200 | 200 | C | C | 150 | C | 180 | C | 212 | C | C | C | C | C | C | C | C | C | C | A | C | C | A | C | C | | | |
| Sulfuric Acid H ₂ SO ₄ | 90% | C | 150 | C | 100 | 200 | 200 | C | C | 70 | C | 160 | C | 212 | C | C | C | C | C | C | C | C | C | C | C | A | C | C | A | C | C | | |
| Sulfuric Acid H ₂ SO ₄ | 93% | C | 140 | C | 100 | 200 | 200 | C | C | 70 | C | 160 | C | 160 | C | C | C | C | C | C | C | C | C | C | C | B | C | C | A | C | C | | |
| Sulfuric Acid H ₂ SO ₄ | 94% | C | 140 | C | 100 | 150 | 200 | C | C | C | C | 160 | C | 160 | C | C | C | C | C | C | C | C | C | C | C | C | B | C | C | A | C | C | |
| Sulfuric Acid H ₂ SO ₄ | 95% | C | 135 | C | 100 | 150 | 200 | C | C | C | C | 160 | C | B to 160 | C | C | C | C | C | C | C | C | C | C | C | C | B | C | C | A | C | C | |
| Sulfuric Acid H ₂ SO ₄ | 96% | C | 130 | C | 100 | 150 | 200 | C | C | C | C | 160 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | B | C | C | B | C | C | |
| Sulfuric Acid H ₂ SO ₄ | 98% | C | 125 | C | C | 150 | 200 | C | C | C | C | 160 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | B | C | C | B | C | C | |
| Sulfuric Acid *H ₂ SO ₄ *ySO ₃ | Fuming | C | C | C | C | C | 200 | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | C | B | C | C | B | C | C | | |
| Sulfurous Acid H ₂ SO ₃ | Sat'd. | C | 180 | 140 | 140 | 210 | 350 | 75 | | 150 | C | 100 | 275 | A | C | C | C | C | C | C | C | C | C | B | A | A | A | C | A | C | | | |
| Surfactants Non-Ionic | | C | C | 100 | C | | | | | | | | B to 125 | | | | | | | | | | | | | | | | | | | | |
| Tall Oil | | | | | | 140 | 280 | 250 | C | 140 | C | B to 70 | 70 | | | | B | B | B | | B | A | A | A | A | B | A | | | A | | | |
| Tannic Acid C ₇₈ H ₅₂ O ₄₆ | 10% | C | 185 | 180 | 140 | 225 | 250 | 70 | 100 | 100 | 100 | 100 | | | A | A | | B | B | C | B | B | A | A | A | A | A | A | A | | | | |
| Tanning Liquors | | | | | | 185 | 140 | | | 70 | 70 | 70 | 200 | | A | A | | B | | | | | A | | A | | | | | | A | | |
| Tar | | | | | | | 250 | 250 | C | C | 70 | 70 | 185 | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Tartaric Acid HOOC(CHOH) ₂ COOH | | | | | | 150 | 140 | 250 | 250 | C | 70 | 200 | 70 | 70 | 275 | A | A | A | C | C | C | C | C | A | A | A | A | A | A | B | | | |
| Terpineol C ₁₀ H ₁₇ OH | | | | | | | C | | | C | 70 | C | C | | | | | | | | | | | | | | | | | | | | |
| Tetrachloroethane CHCl ₂ CHCl ₂ | | | | | | | | 250 | 400 | C | C | C | C | 70 | | | | | | | | | | | | | | | | | A | A | |
| Tetrachloroethylene C ₂ C:CCl ₂ | | C | | | | | | 275 | 350 | C | C | C | C | 70 | | | | | | | | | | | | | | | | | | | |
| Tetraethyl Lead Pb(C ₂ H ₅) ₄ | | | | | | | | 73 | 280 | 350 | C | 70 | C | | 70 | 275 | A | A | | B | B | | A | | | A | A | | | | | | |

Chemical Resistance Guide for Valves and Fittings

| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | | | METALS | | | | | | | | | | | | | | | | | |
|---|---------------|---------------------------------|------|-----|-----|------|--------------------------------|------|---------|----------|----------|--------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------------------|----------|---------|----------|-------|----------|-------------|----------|--------|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYDROXYL | NEOPRENE | FLUOROCARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NI PLATED DUCTILE 400 SERIES S.S. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER |
| Tetrahydrofuran C ₄ H ₈ O | | C | C | C | C | C | | C | C | C | C | C | 275 | | | | | | | | | | | | | | | | | | |
| Tetralin C ₁₀ H ₁₂ | | | | | | 200 | C | C | | C | C | | | | | | | | | | | | | | | | | | | | |
| Tetra Sodium Pyrophosphate NaP ₂ O ₇ •10H ₂ O | | | | | 140 | | | | | | | | A | | | | | | | | | | | | | | | | | | |
| Thionyl Chloride SOCl ₂ | | | | C | | | | C | | C | | 275 | A | | | | | | | | | | | | | | | | | | |
| Thread Cutting Oils | | | | 73 | 200 | 350 | C | 70 | | 70 | | | A | | | | | | A | A | A | | A | A | A | A | A | A | A | | |
| Titanium Tetrachloride TiCl ₄ | | | | C | 150 | | C | | C | C | 185 | 275 | A | C | C | | | | C | | | | B | | B | B | | | | | |
| Toluene (Toluol) CH ₃ C ₆ H ₅ | C | C | C | C | 175 | 200 | C | | C | C | 70 | 275 | | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | |
| Tomato Juice | | | | 180 | | 200 | 350 | 200 | C | C | 70 | 200 | | B | | | C | C | B | | | A | A | A | A | A | A | A | A | | |
| Transformer Oil | | | | 120 | 140 | | 300 | C | 140 | | C | 140 | 550 | A | A | | | | A | A | | | A | A | A | A | A | A | A | | |
| Transformer Oil DTE/30 | | | | | | 300 | C | 140 | C | C | | 550 | A | A | | | | A | A | | | A | A | A | A | A | A | A | A | | |
| Tributyl Citrate C ₁₈ H ₃₂ O ₇ | | | | | 73 | | | | | | | | | | | | | | | | | | | | | | | | | | |
| Tributyl Phosphate (C ₄ H ₉) ₃ PO ₄ | | | | C | 73 | 300 | 70 | C | C | C | | | B | B | B | | | A | A | A | | B | A | | A | A | | | | | |
| Trichloroacetic Acid CCl ₃ COOH | | | | 150 | 140 | 125 | 200 | 70 | B to 70 | 70 | 70 | C | | A | B | C | | C | C | C | | C | B | | B | | | | | | |
| Trichloroethylene CHCl:CCl ₂ | C | C | C | C | 280 | 200 | C | C | C | C | 185 | 275 | A | A | A | A | A | B | B | B | | A | A | A | A | A | A | A | A | | |
| Triethanolamine (HOCH ₂ CH ₂) ₃ N | | 70 | | | 73 | 125 | | 70 | 70 | 150 | 70 | C | 275 | | C | C | | C | C | C | C | C | A | | A | A | | | | | |
| Triethylamine (C ₂ H ₅) ₃ N | | | | | 140 | 125 | | | 140 | | 70 | 200 | | | A | A | | | | | | | | | | | | | A | | |
| Trimethylpropane (CH ₂ OH) ₃ C ₃ H ₅ | | | | 73 | | | | 180 | 200 | 160 | 300 | | | | | | | | | | | | | | | | | | | | |
| Trisodium Phosphate N ₃ P ₂ O ₇ •12H ₂ O | 70 | 185 | 185 | 140 | 280 | 350 | 70 | 70 | 185 | 70 | 185 | 550 | A | C | C | | | B | B | | A | | A | A | A | A | A | A | | | |
| Tung Oil | | | | | | | C | 100 | 100 | 100 | 100 | | | B | B | B | | B | B | B | | B | A | A | A | A | A | A | | | |
| Turpentine | | 73 | C | 140 | 280 | | C | 70 | C | C | 150 | 550 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | | |
| Urea CO(NH ₂) ₂ | | 185 | 180 | 140 | 250 | | 210 | 140 | 140 | 140 | 185 | 550 | | B | B | | C | C | C | | | A | A | B | C | | | C | | | |
| Urine | | | | 180 | 140 | | 400 | 210 | 140 | 140 | 140 | 70 | | | | C | C | C | | | A | A | A | A | A | | | | | | |
| Varnish | | | | | 250 | 350 | C | 70 | | C | 70 | | | A | A | B | B | C | C | C | | B | A | A | A | A | A | A | A | | |
| Vaseline (Petroleum Jelly) | | | | 150 | C | | 300 | C | 140 | 70 | 140 | 70 | 550 | | | | A | A | A | | | A | A | A | A | A | A | A | A | | |
| Vegetable Oil | C | C | 100 | C | 275 | 300 | C | 70 | 70 | 70 | 200 | 550 | A | A | | | | A | A | | | A | A | A | A | A | A | A | A | | |
| Vinegar | 73 | 180 | 180 | 140 | 225 | 300 | 180 | C | 200 | 70 | C | 550 | | C | C | C | C | C | C | C | | A | A | A | A | A | A | A | C | B | |
| Vinyl Acetate CH ₃ COOCH:CH ₂ | | | | C | C | 250 | 350 | 70 | 70 | C | C | 275 | | B | B | | B | B | B | | | A | A | B | | | | | | | |
| Water, Acid Mine H ₂ O | | 185 | | 140 | 230 | 400 | 200 | 180 | 180 | 160 | | | | A | C | C | C | C | C | C | C | A | A | A | A | B | B | B | C | C | |

Chemical Resistance Guide for Valves and Fittings



| CHEMICALS AND FORMULA | CONCENTRATION | PLASTICS AT MAX. TEMPERATURE °F | | | | | SEAL MATERIALS AT MAX. TEMP °F | | | | | METALS | | | | | | | | | | | | | | | | | | | | | |
|---|---------------|------------------------------------|------|-----|-----|------|-----------------------------------|------|--------|---------|----------|---------------|------|----------|-----------------|----------------|-----------------|-------|-----------|--------------|--------------|------------|-----------------------|----------------|----------|---------|----------|-------|----------|-------------|----------|--------|--|
| | | ABS | CPVC | PP | PVC | PVDF | TEFLON | EPDM | BUNA-N | HYPALON | NEOPRENE | FLUORO-CARBON | PEEK | GRAPHITE | BRONZE (85% Cu) | SILICON BRONZE | ALUMINUM BRONZE | BRASS | GRAY IRON | DUCTILE IRON | CARBON STEEL | 3% NI/IRON | NIPLATED DUCTILE IRON | 400 SERIES SS. | 316 S.S. | 17-4 PH | ALLOY 20 | MONEL | STELLITE | HASTELLOY C | ALUMINUM | COPPER | |
| Water, Deionized H ₂ O | 70 | 210 | 180 | 140 | 280 | 400 | 200 | 70 | | 160 | | | | A | B | B | C | C | C | C | C | C | C | B | A | A | A | A | A | A | | | |
| Water, Distilled H ₂ O | 70 | 210 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | | | | A | A | A | B | B | C | C | C | B | C | A | A | A | A | B | A | A | A | | |
| Water, Potable H ₂ O | 70 | 210 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | | | 550 | A | A | A | A | A | B | B | B | A | B | A | A | A | A | A | A | B | A | | |
| Water, Salt H ₂ O | 70 | 210 | 180 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | | | | A | B | B | B | C | C | C | C | B | C | B | A | A | A | A | B | A | C | B | |
| Water, Sea H ₂ O | 70 | 210 | 73 | 140 | 280 | 400 | 250 | 180 | 200 | 160 | | | | A | B | B | B | C | C | C | C | B | C | B | B | A | A | A | C | A | C | B | |
| Water, Soft H ₂ O | 70 | | | | 200 | 400 | 250 | 180 | 200 | 160 | | | | A | A | A | A | B | C | C | B | B | C | A | A | A | A | A | A | A | A | A | |
| Water, Waste H ₂ O | 70 | 185 | 180 | 140 | 230 | 400 | 200 | | | | 70 | | A | B | B | B | B | B | B | B | B | B | B | A | | A | A | A | B | B | | | |
| Whiskey | | 185 | 150 | 140 | 200 | 350 | 200 | 140 | 140 | 140 | 140 | 140 | | C | C | B | | C | C | C | | C | B | A | | A | A | A | A | A | A | A | |
| White Liquor | | 185 | | 140 | 230 | | | 140 | 140 | 140 | | | 550 | C | C | C | | C | C | C | | C | A | | A | A | A | | | | | | |
| Wine | | 185 | 150 | 140 | 200 | 350 | 170 | 140 | 140 | 140 | 140 | 550 | | C | C | | | C | C | C | | C | B | A | | A | A | | | | | | |
| Xylene (Xylo) C ₆ H ₄ (CH ₃) ₂ | C | C | C | C | 200 | 350 | C | C | C | 150 | 275 | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | A | | | |
| Zinc Acetate Zn(C ₂ H ₃ O ₂) ₂ •2H ₂ O | | | | | 250 | | 180 | 70 | 70 | 160 | 70 | | C | C | C | C | C | C | C | C | C | C | A | A | A | | | | | | | | |
| Zinc Carbonate ZnCO ₃ | | | | | | | | 100 | 100 | | | 275 | B | B | | | | | | | | | | B | | A | B | | | | | | |
| Zinc Chloride ZnCl ₂ | | 185 | 180 | 140 | 280 | 400 | 180 | 70 | 200 | 160 | 200 | 275 | A | C | C | C | | C | C | C | | C | C | B | B | A | A | | | | | | |
| Zinc Nitrate Zn(NO ₃) ₂ •6H ₂ O | | | | 140 | 280 | | 180 | 140 | 200 | | 200 | 275 | A | | | | | | | | | | | A | A | A | | | | | | | |
| Zinc Sulfate ZnSO ₄ •7H ₂ O | | 185 | 180 | 140 | 280 | 400 | 180 | 140 | 200 | 140 | 200 | 275 | A | C | C | B | | C | C | C | B | C | A | A | A | A | A | A | A | A | A | | |

NIBCO INC., its marketing companies and distributors, and the authors of and contributors to this publication specifically deny any warranty, expressed or implied, for the accuracy and/or reliability of the fitness for any particular use of information contained herein.

To the best of our knowledge the information contained in this publication is accurate, however, we do not assume any liability whatsoever for accuracy or completeness of such information. Moreover, there is a need to reduce human exposure to many materials to the lowest practical limits in view of possible long-term adverse effects. To the extent that any hazards may have been mentioned in this publication, we neither suggest nor guarantee that such hazards are the only ones which exist. Final determination of the suitability of any information or product for the use to be contemplated by the user, the manner of that use, and whether there is any infringement of patents is the sole responsibility of the user. We recommend that anyone intending to rely on any recommendation or to use any equipment, processing technique or material mentioned in this publication should satisfy himself as to such suitability and that he meets all applicable safety and health standards. We strongly recommend that users seek and adhere to manufacturer's or supplier's current instructions for handling each material they use.

globally connecting you at all levels

It's a new age of business, and a new way at NIBCO. From Elkhart, Indiana to Lodz, Poland, and points beyond, our company has integrated manufacturing, distribution, and networked communications to provide a seamless source of information and service, 24 hours a day, 7 days a week. But this integration hasn't happened overnight. It's been part of a long-term strategic process that has pushed us to reconsider every aspect of our business. The result? We're a vertically integrated manufacturer with the products and systems in place to deliver low cost and high quality. NIBCO's products are manufactured under a Quality Management System conforming to the current revision of ISO-9001 International Standards. We know the flow control industry is only going to get more demanding, and we are more than ready. We will continue to lead. That's what NIBCO is all about.

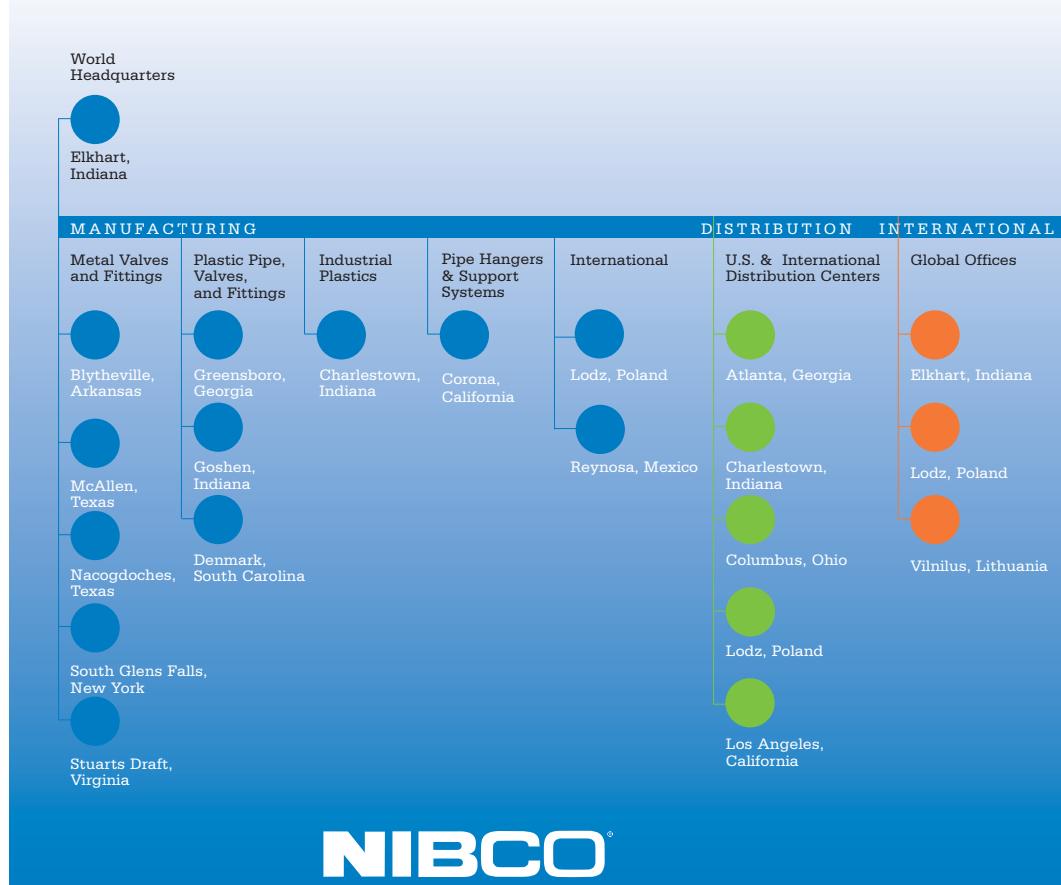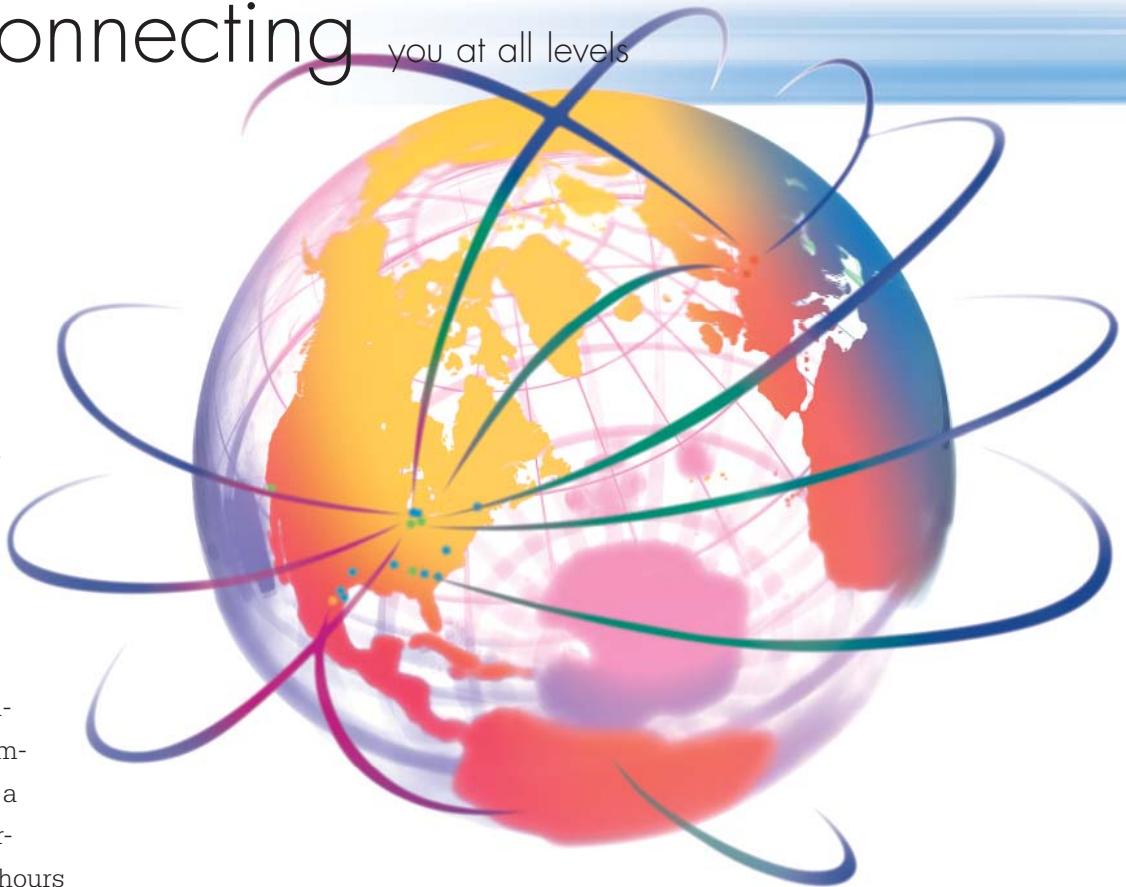

INTRODUCING NIBCO® SYSTEMS

NIBCO® NEXT-Pure™ PEX potable water system • NIBCO® Press System™

FITTINGS



- Wrot and cast copper pressure and drainage fittings
- Cast copper alloy flanges
- ABS and PVC DWV fittings
- Schedule 40 PVC pressure fittings
- CPVC CTS fittings
- CPVC CTS-to-metal transition fittings
- Schedule 80 PVC and CPVC systems
- CPVC metric piping systems.

VALVES & ACTUATION



- Pressure-rated bronze, iron and alloy-iron gate, globe and check valves
- Pressure-rated bronze ball valves
- Boiler specialty valves
- Commercial and industrial butterfly valves
- Circuit balancing valves
- Carbon and stainless steel ball valves
- ANSI flanged steel ball valves
- Pneumatic and electric actuators and controls
- Grooved ball and butterfly valves
- High performance butterfly valves
- UL/FM fire protection valves
- MSS specification valves
- Bronze specialty valves
- Low pressure gate, globe, check and ball valves
- Frostproof sillcocks
- Quarter-turn supply stops
- Quarter-turn low pressure valves
- PVC ball valves
- CPVC CTS ball valves
- Just Right® recirculating valves.


CHEMTROL®



- Thermoplastic pipe, valves and fittings in PVC, Corzan® CPVC, polypropylene and PVDF Kynar®
- Chem-Aire® thermoplastic compressed air piping systems
- Pneumatic and electric actuation systems.

Corzan® is a registered trademark of The Lubrizol Corporation • Kynar® is a registered trademark of ATOFINA Chemicals, Inc.

TOLCO™



- Pipe attachments
- Structural attachments
- Pipe rollers
- Threaded products and accessories
- Seismic components
- Vibration isolation
- Standard and specialty supports
- TOL-Strut® channel and components.

eNIBCO



- EDI—Electronic Data Interchange
- VMI—Vendor Managed Inventory
- NIBCO.com
- NIBCOpartner.com

NIBCO®
AHEAD OF THE FLOW®

NIBCO INC.

WORLD HEADQUARTERS

WEB: www.nibco.com

1516 MIDDLEBURY STREET
ELKHART, IN 46516-4740
USA

DOMESTIC CUSTOMER SERVICE
PHONE: 800.234.0227
FAX: 800.234.0557

TECHNICAL SERVICE
PHONE: 888.446.4226
FAX: 888.336.4226

INTERNATIONAL OFFICE
PHONE: +1/574.295.3221
FAX: +1/574.295.3455